

Neutron Powder Diffraction and Novel Materials


Alan Hewat



ILL Grenoble

8th ZuoZ Summer School on Neutron Scattering, 5-11 August 2000

Why Use Neutron Powder Diffraction ?

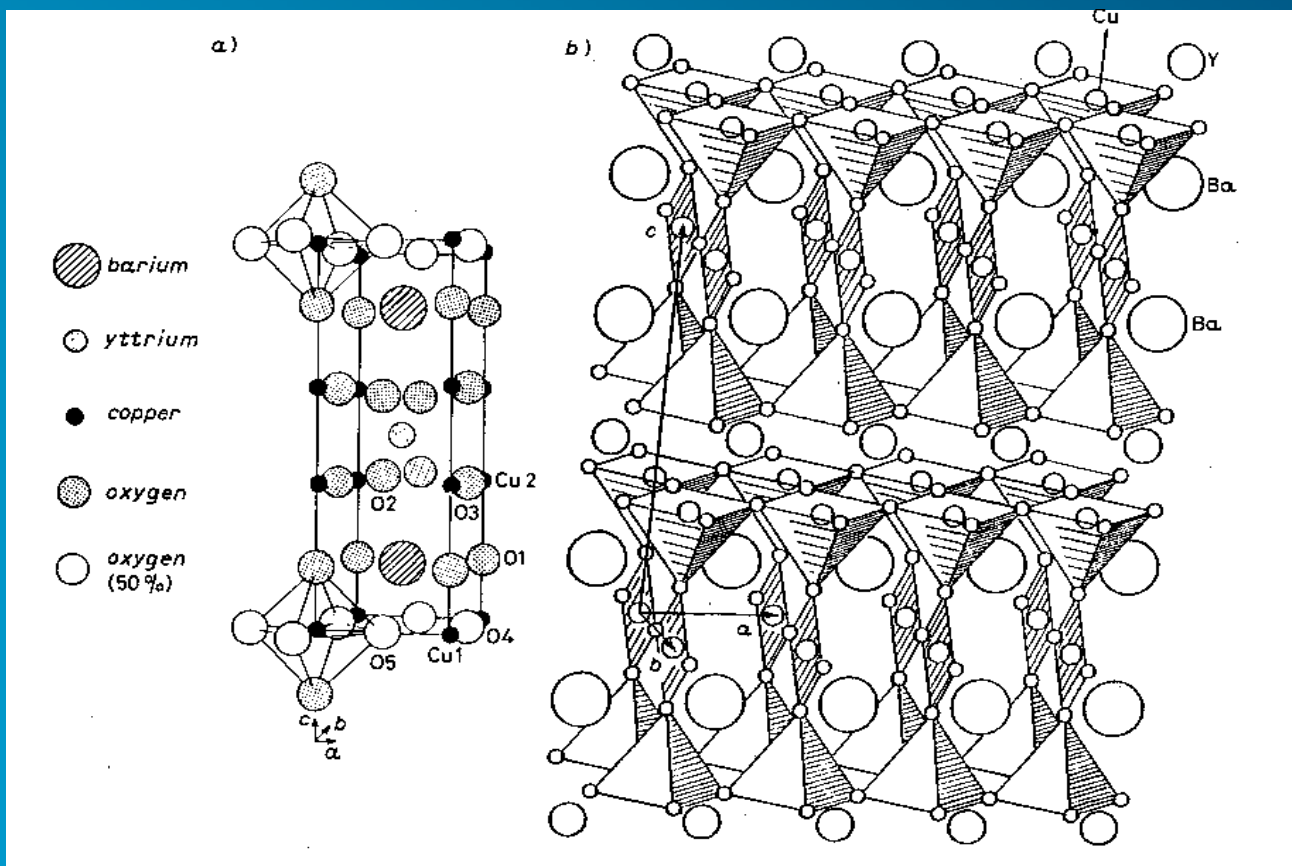


- Structure of the 90K high T_c superconductor
 - Left -by X-rays (Bell labs & others)
 - Right -by Neutrons (many neutron labs)
- The neutron picture gave a very different idea of the structure - important in the search for similar materials.

YBa₂Cu₃O₇ drawing from Capponi et al. Europhys Lett 3 1301 (1987)



Why Neutrons ?

- Relative Scattering Powers of the Elements

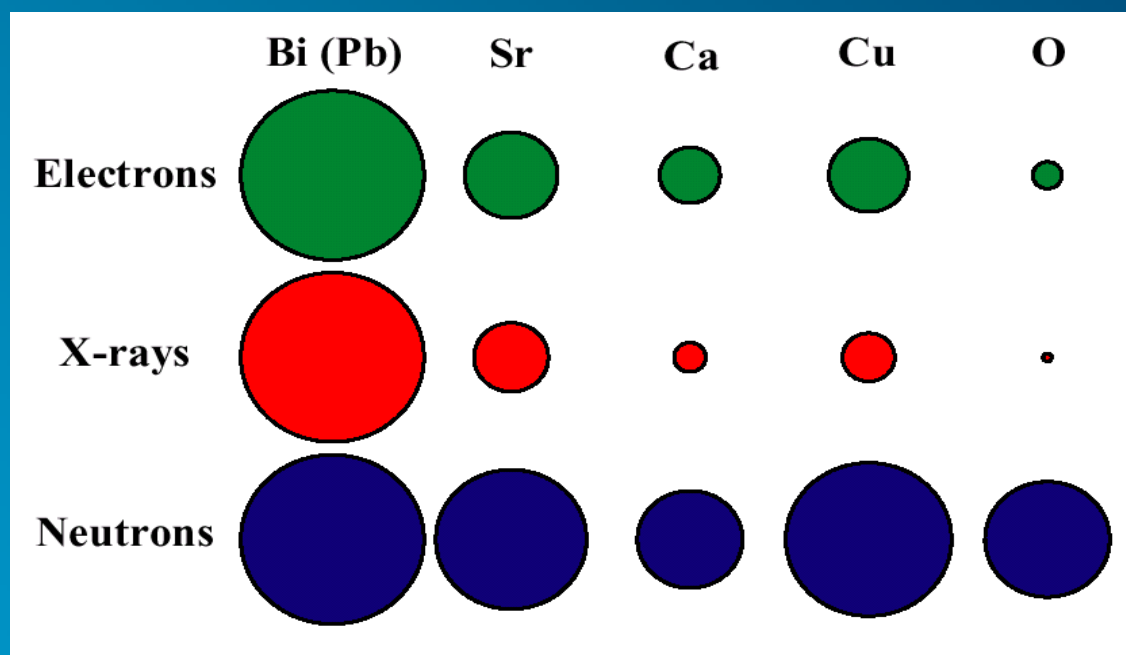


- Neutrons scatter strongly from light elements
(Because neutron scattering is a nuclear interaction)



Why Neutrons ?

- Neutrons are unique for Magnetic Structures

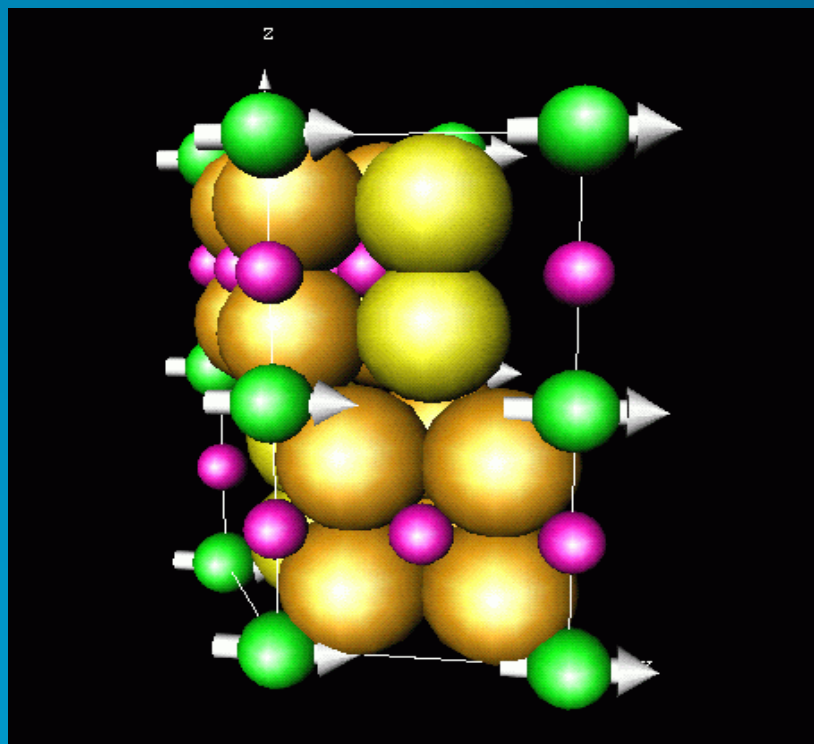

- H.M. Rietveld

Structure of Magnetic Materials

MnTa₄S₈ - the famous example given in the original Rietveld manual






Why Powders ?

- ...Well, if you don't have a single crystal...
- For many new, interesting materials, single crystals are not available
 - Zeolites, Superconductors, GMR materials...
- And many other materials are not really single crystals
 - At least not at 0 K, the most important temperature



Why Powders ?

- Destructive Phase T/Ns
 - Classical Perovskite transitions
Small displacements of light atoms
 - Subtle changes in the powder 'profile'
- interest of "Profile Refinement"
- And no single crystals

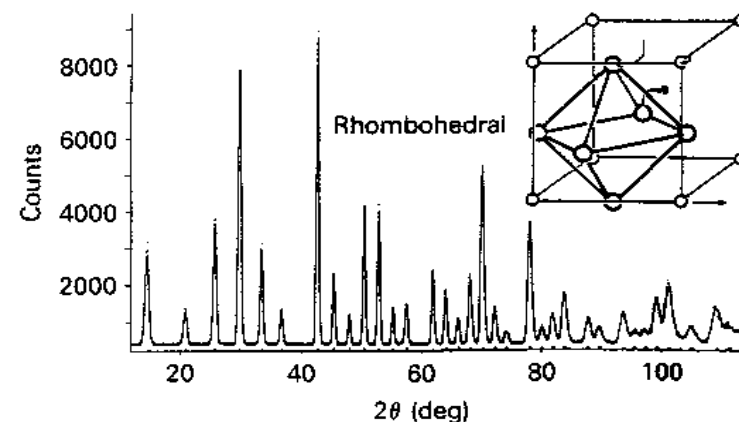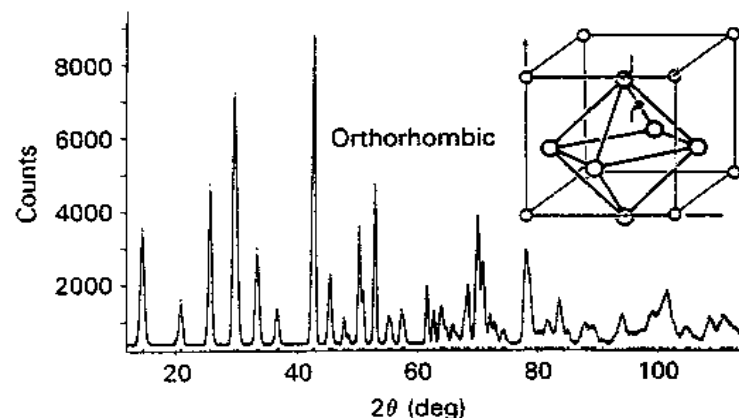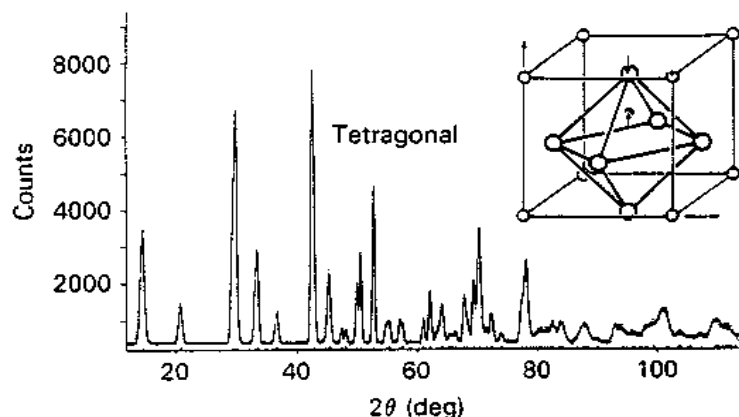



Why Rietveld Refinement ?

- Strongly overlapping reflections
 - Previously, integrated intensities were obtained for groups of overlapping reflections.
- Key to success of RR
 - inclusion of all the information
 - refinement of physically meaningful parameters
(reduction of correlation between parameters)



Why not X-ray Powder Diffraction ?

(Question from Bruno Dorner)

- Magnetic structures... not possible with x-ray powders
- X-rays best (synchrotrons) for **SOLVING** structures

Easier to find the heavy atoms first

All atoms are 'equal' for neutrons

- Neutrons are best for **REFINING** structures

Few systematic errors (average over big samples etc...)

Easier sample environment (low temperatures etc...)

- Interest of very precise structure measurements

Precise bond lengths


Study charge ordering, metal-insulator transitions...



Valence Sum Calculations

What is the valence of Cu in Cu_4O_3 ? (Exercise)

O'Keeffe, M. Bovin, J. Am. Miner 63 180 (1978)

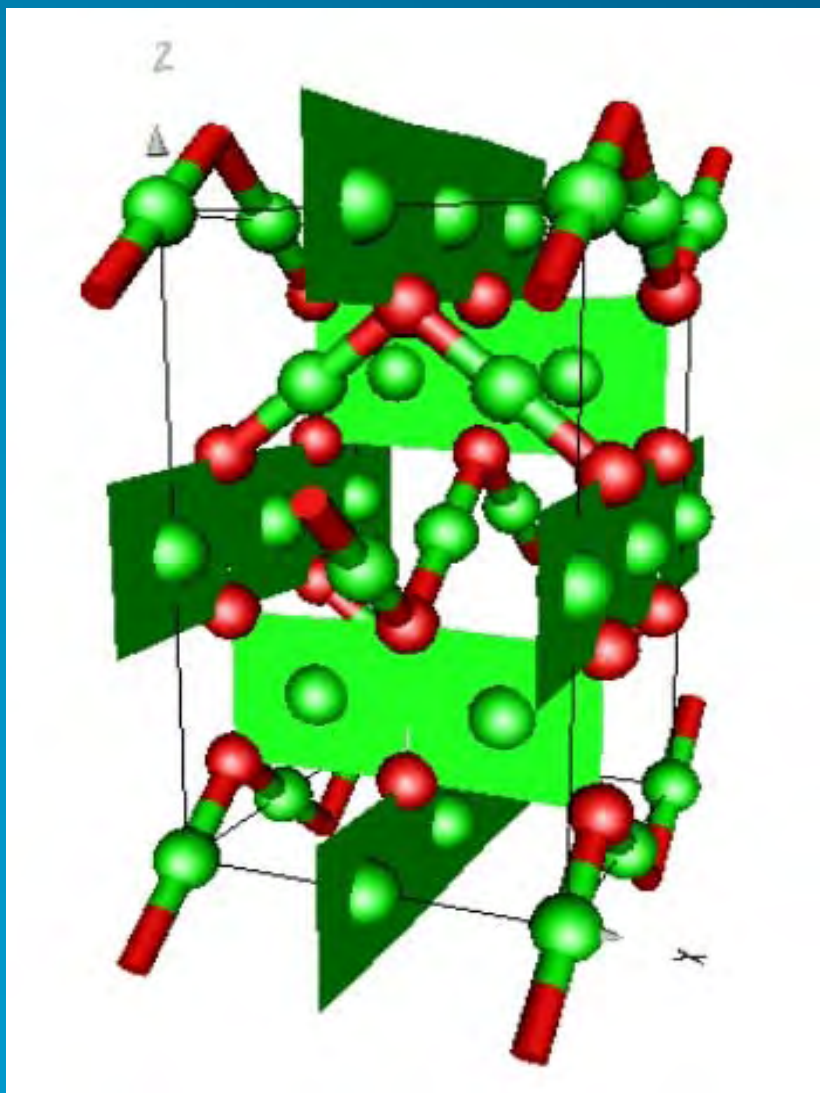

- Average Cu valence = $2 \times 3/4 = 1.5$
 - Just from the formula Cu_4O_3
- 2 types of Cu
 - Cu^+ at (0,0,0) with 2 oxygens
 - Cu^{2+} at (0,0,1/2) with 4 oxygens
- Valence Sum $V = \sum_i [\exp(\text{Ro} - \text{Ri}) / B]$
 - Ri = Cu-Oi bond lengths
 - $\text{Ro} = 1.610$ for Cu^+ to O^{2-}
 - $B = 0.370$
- Calculate Ri bond lengths & hence V

Hints:




 - All bonds approx equal
 - Each bond contributes ~ 0.5



Valence Sums & "Charge Transfer"

Most cited neutron papers - "charge reservoir" concept in oxide superconductors

- Superc. $\text{YBa}_2\text{Cu}_3\text{O}_7$
- Non-superc. $\text{YBa}_2\text{Cu}_3\text{O}_6$
- Charge Reservoir

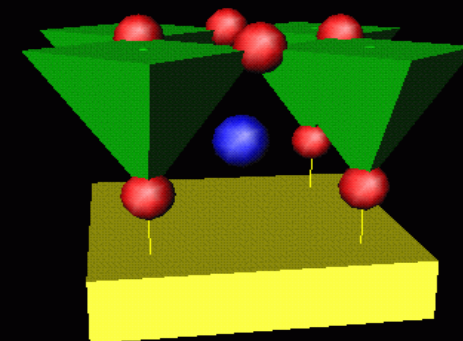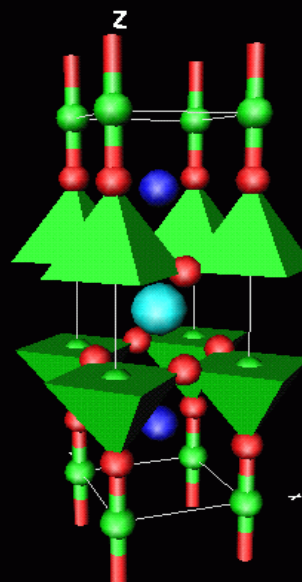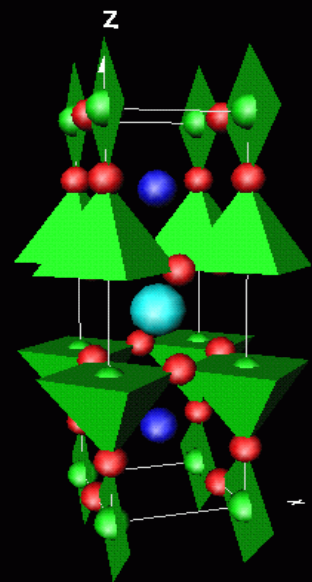

- Cava, R. J. et al. (1990). Physica C. 165: 419 (Bell labs/CNRS/ILL)
- Jorgensen, .D. et al. (1990) Phys. Rev. B41, 1863 (Argonne)



Valence Sums & "Charge Transfer"

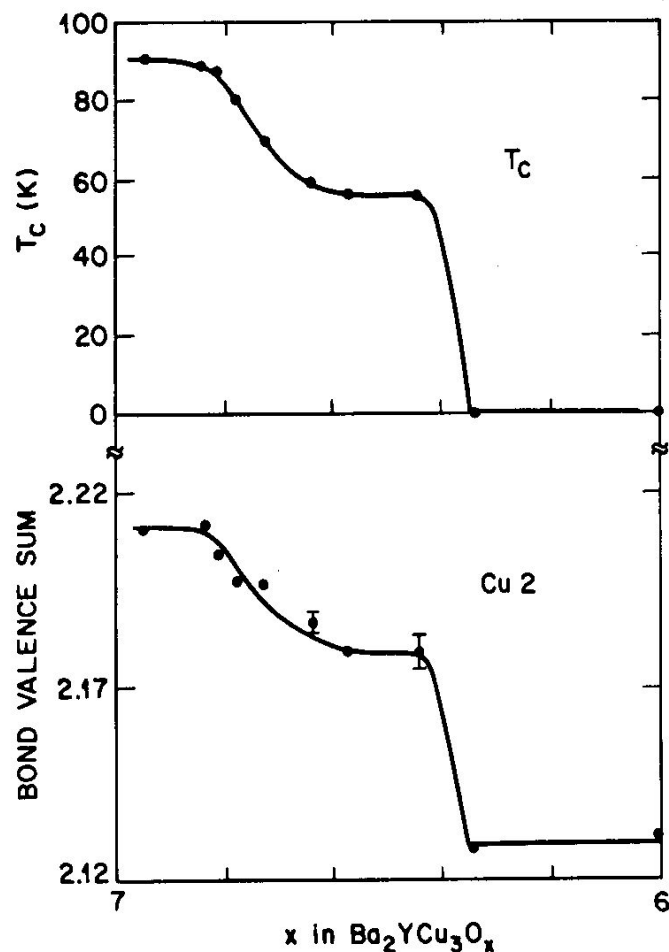


Fig. 16. Comparison of T_c and bond valence sum around the plane copper as a function of oxygen stoichiometry.


- Relation between bond lengths, charge transfer and superconducting T_c
- The "Charge Reservoir" concept encouraged many chemists to successfully search for similar materials with different charge reservoir layers

Popularity of Neutron Powder Diffraction

Alan Hewat




ILL Grenoble

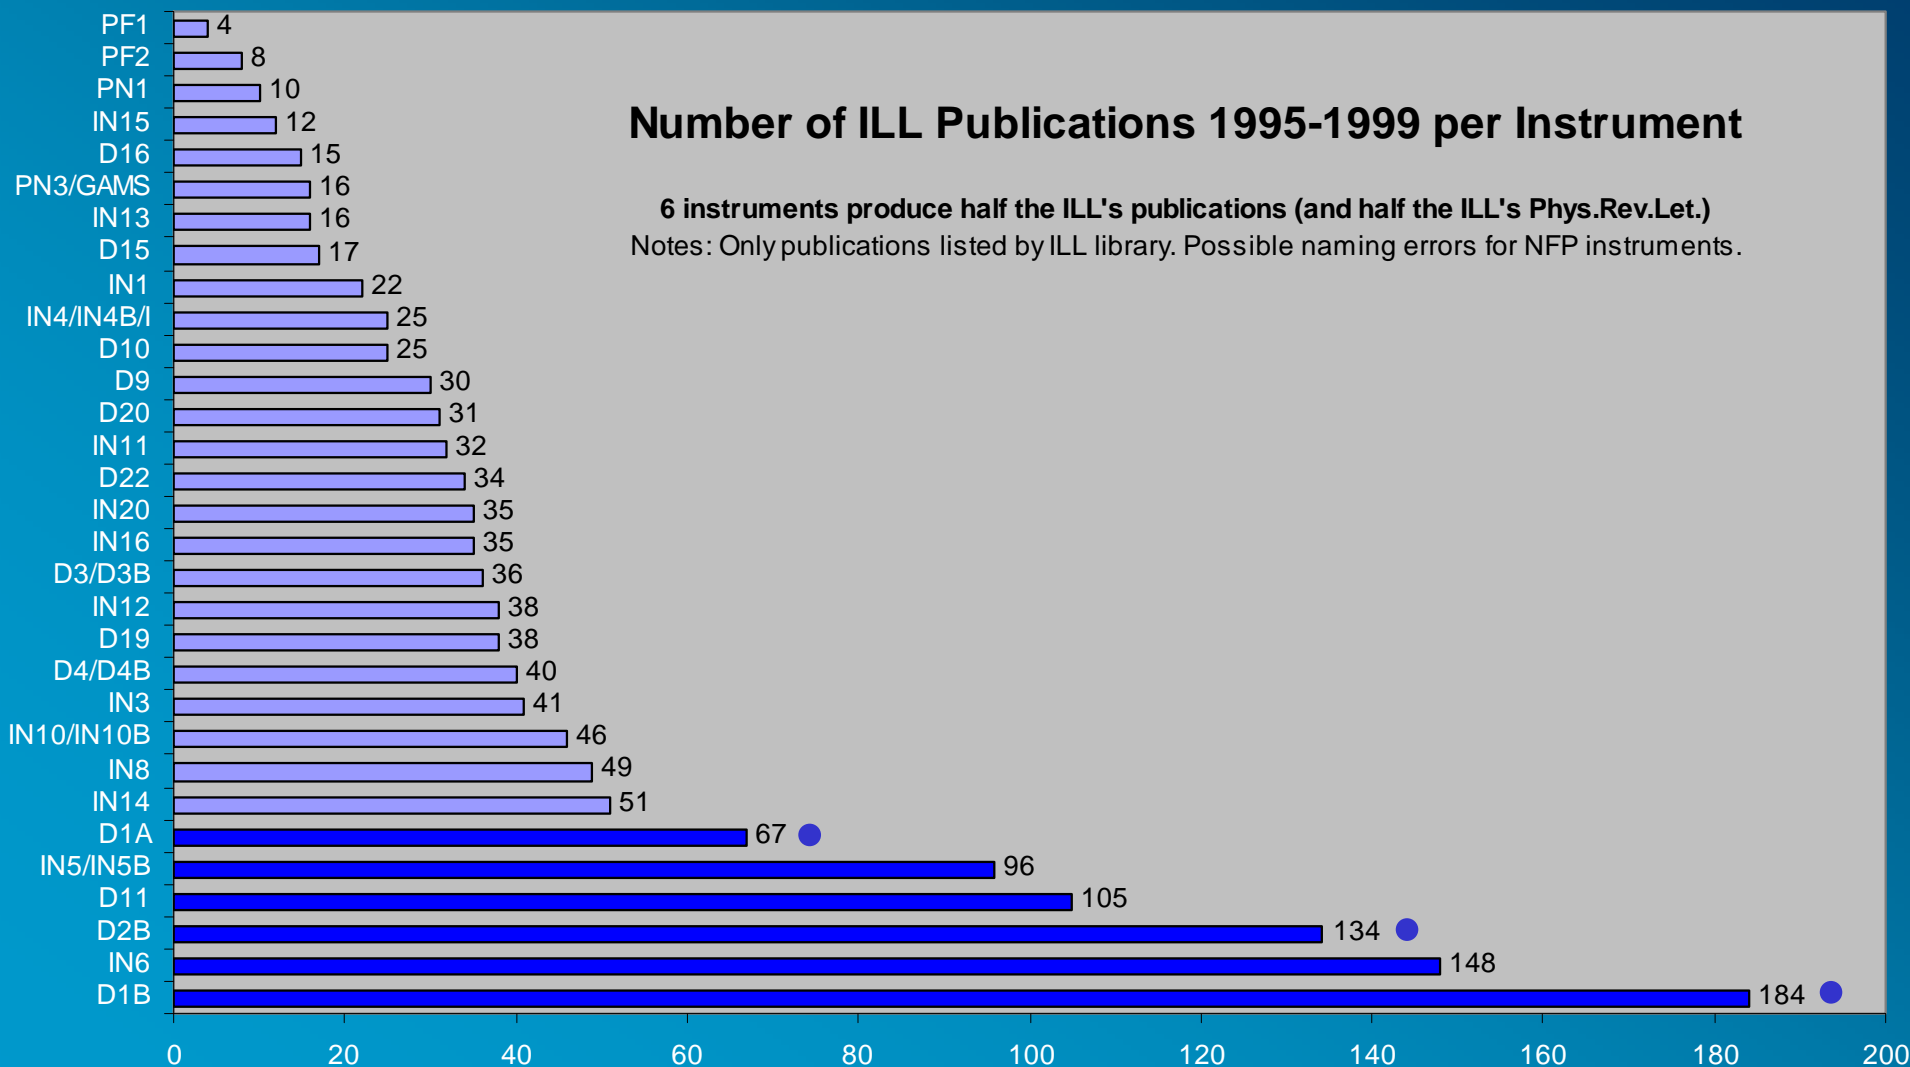



Powder Diffractometers are Simple

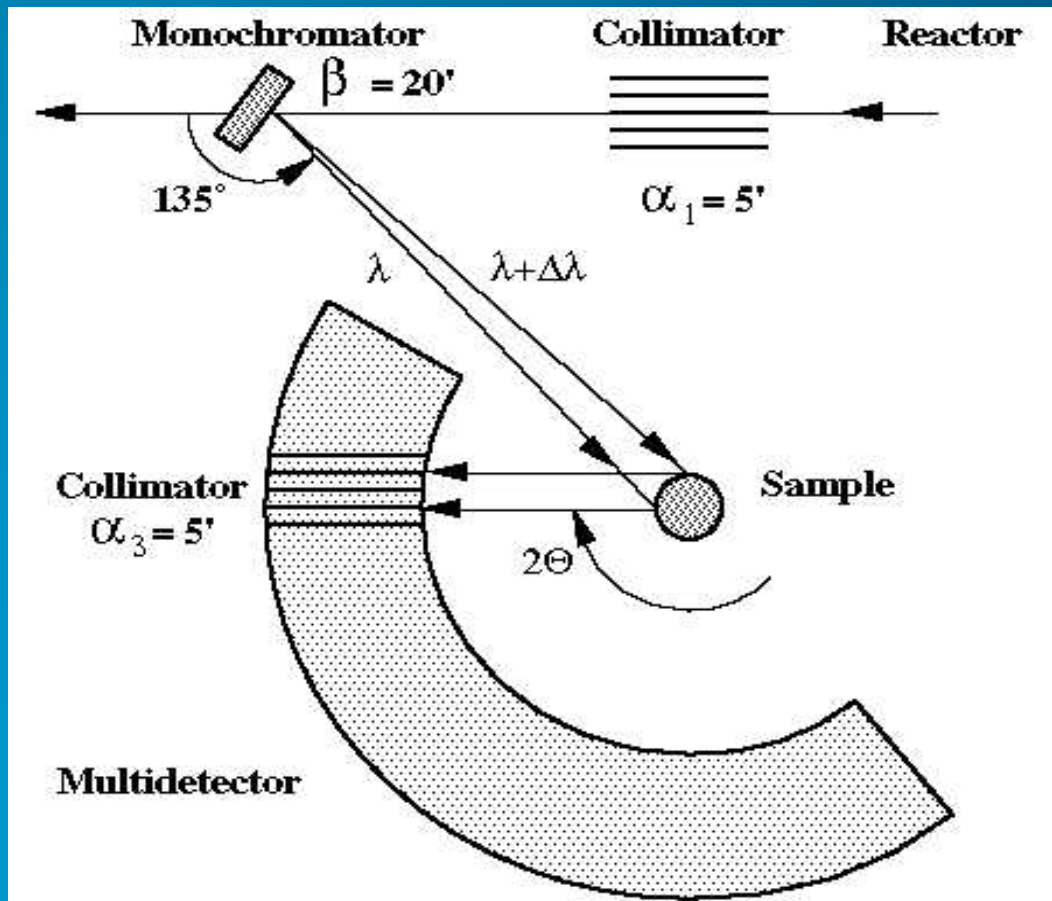


- A continuous neutron source
- Incident collimation
- A Monochromator
- The Sample & environment
- Scattering collimation
- A Detector



Alternative TOF techniques

- Time-of-flight diffractometers (E. Steichele, Munich)
 - J. Jorgensen, Argonne (SEPD, GPPD)
 - B. Fender & A. Hewat, Rutherford Lab.

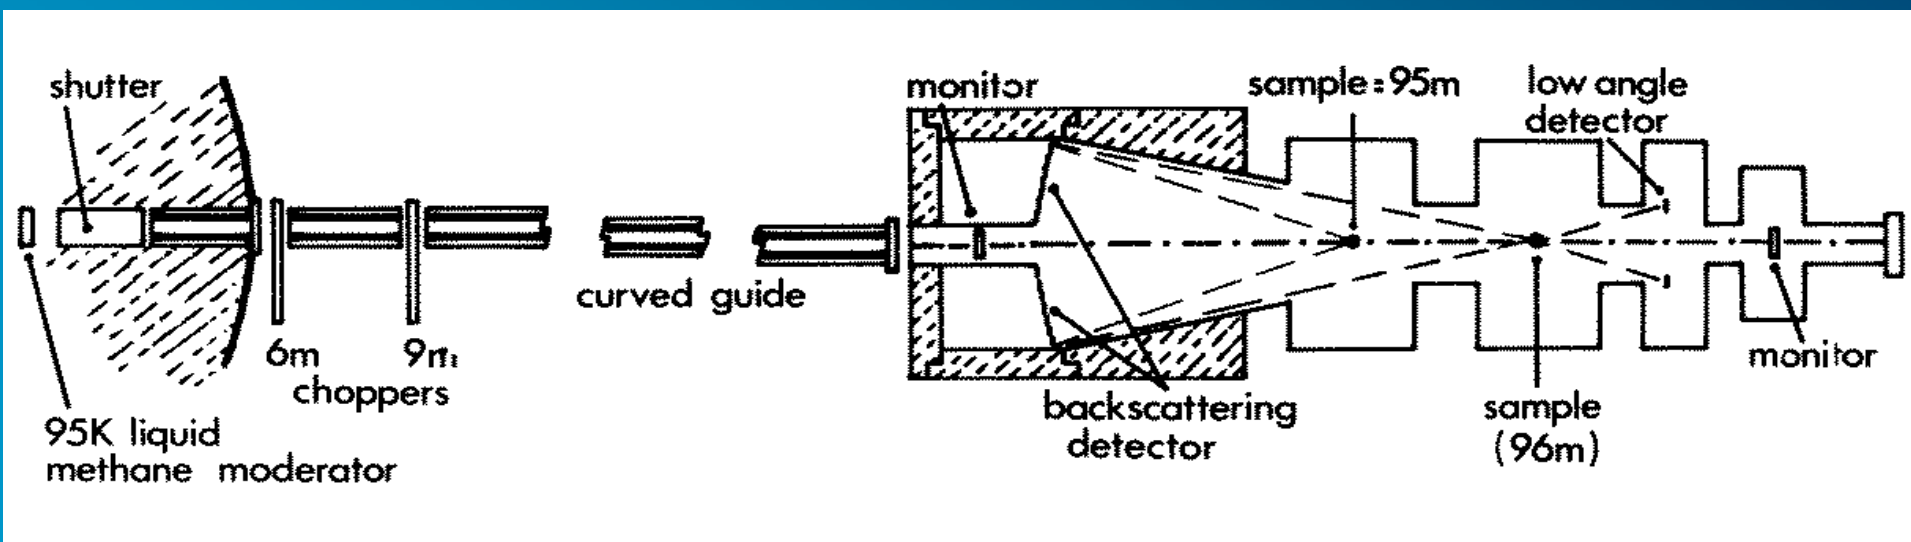

- HRPD ISIS (High Resolution Powder Diffractometer)
W. David et al.




Early Days at ILL Grenoble (1972)



- First ILL Powder Diffractometers D1A, D2
 - Single detector
 - Small soller collimator
 - Shared monochromator
- -High Resolution, BUT
- -Very Low Intensity



Early Days at ILL Grenoble (1974)

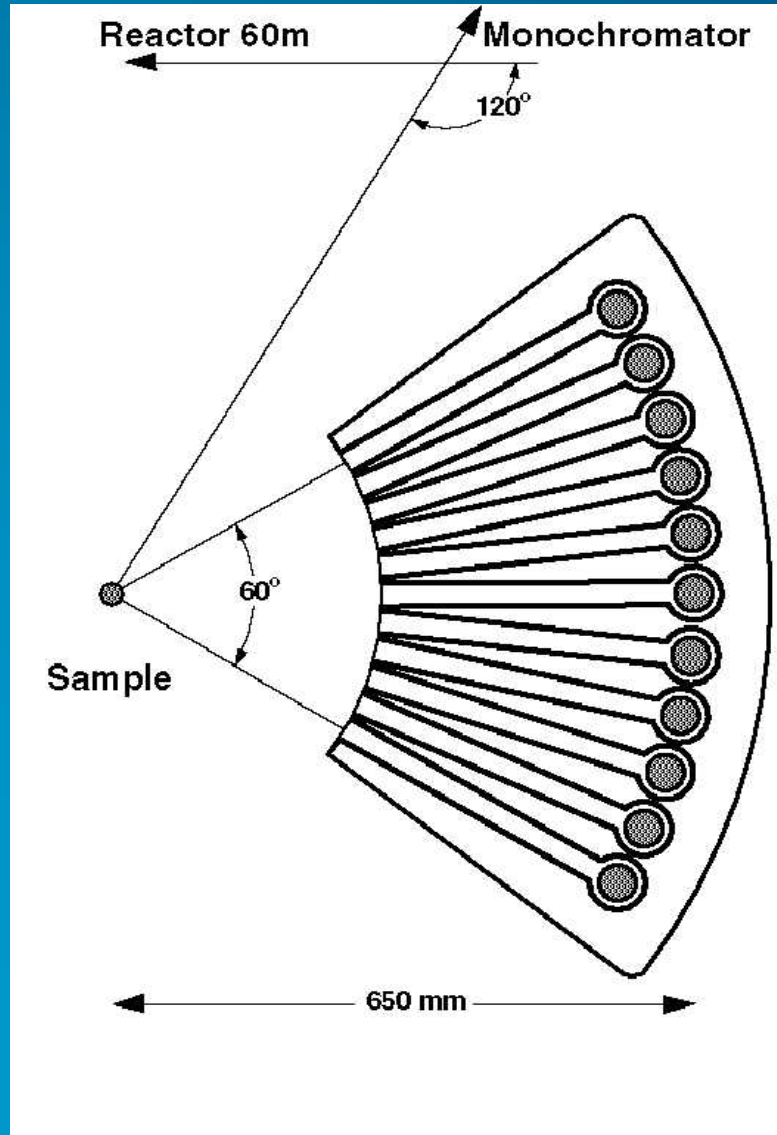


- Orders of Magnitude Improvement - D1A

- Multiple detectors
- Large efficient collimators
- Focussing Monochromator




ILL Grenoble

Comparison of D1A with D2 (1974)

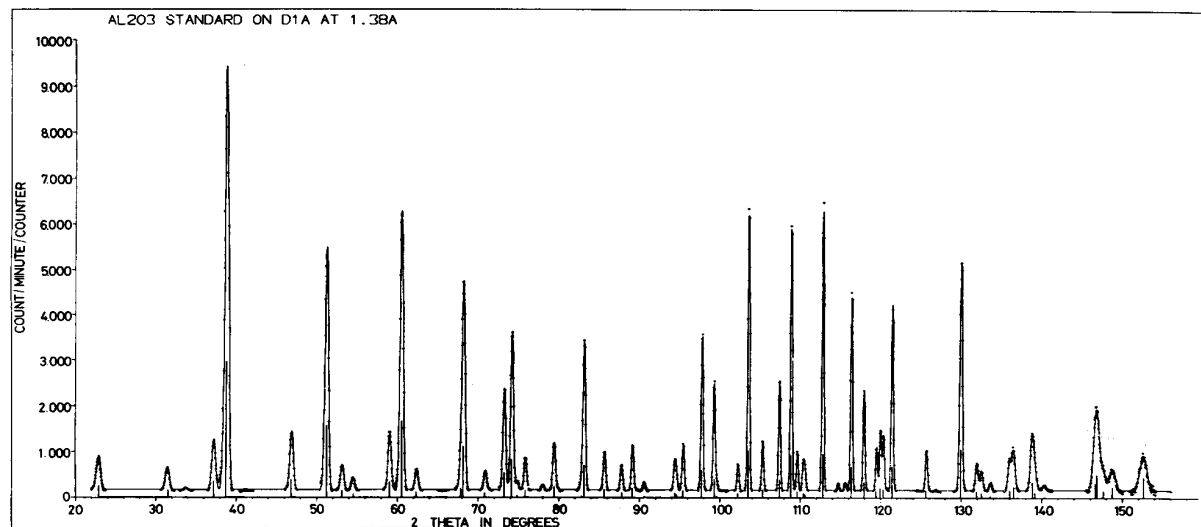

(a)

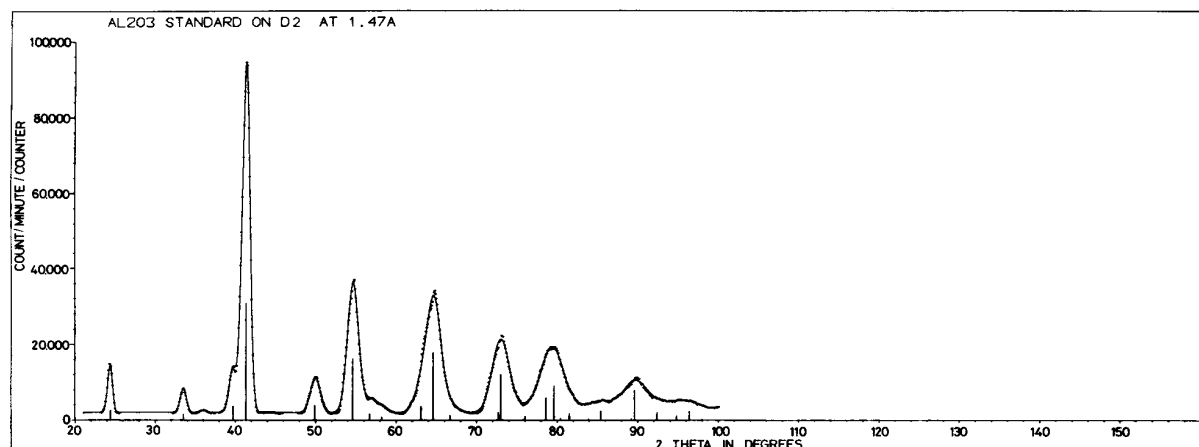

(b)

- The same Al₂O₃ sample on D1A (top) and the old D2 at ILL.



Early Days at ILL Grenoble (1973)



- New types of PSD's
 - Position Sensitive Detector used for the first time
 - Very Fast machine (Faster than X-rays)
 - Moderate Resolution
- In-situ Chemistry with RR (Convert, Riekel ...)




The Second Generation (80's)



- High Resolution with Very Large Detector banks (D2B, ILL)




The Second Generation (80's)

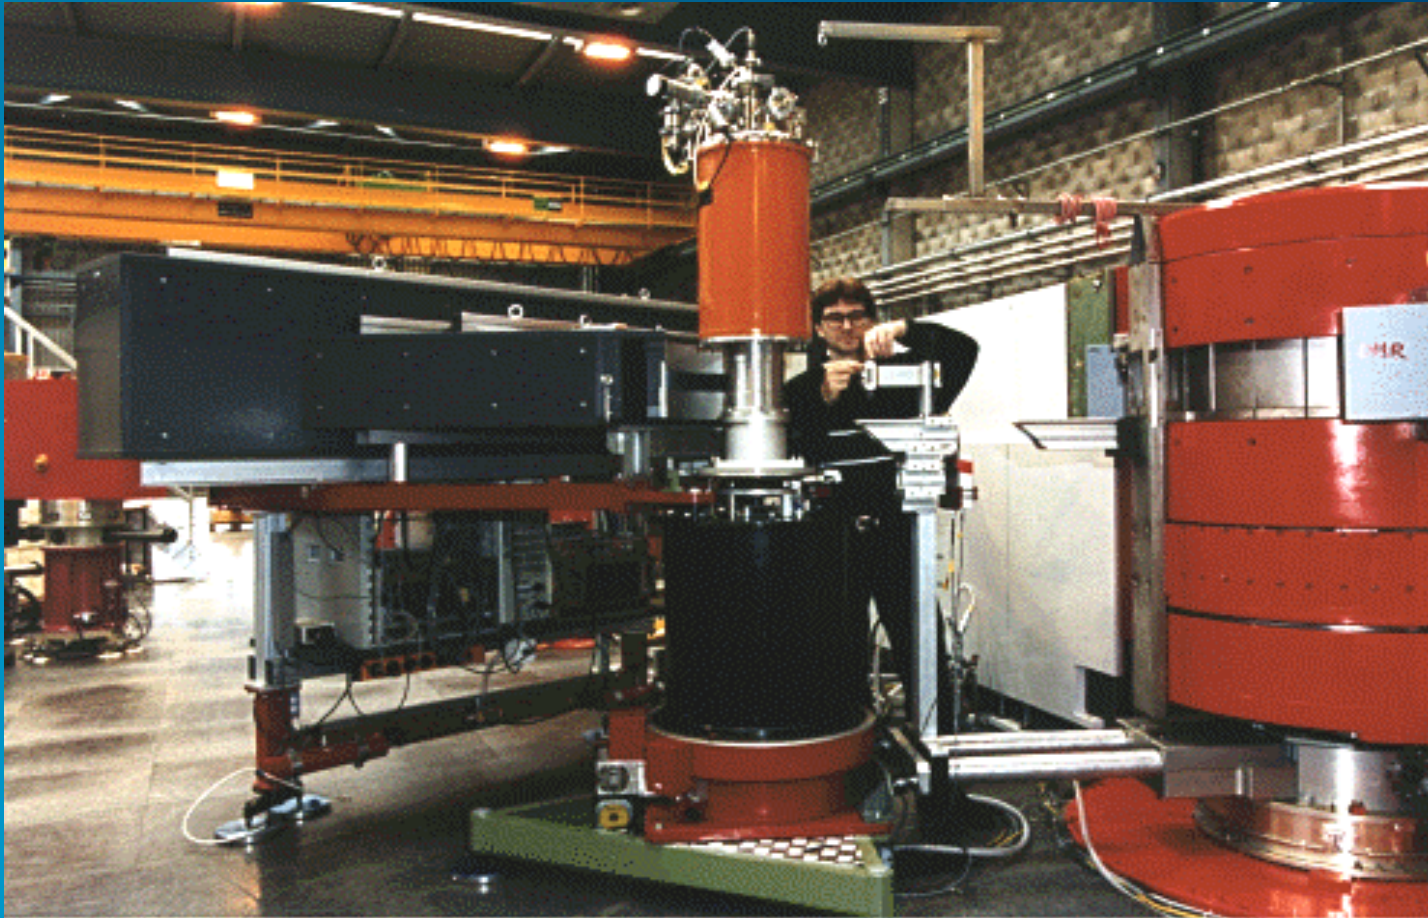

- DMC high efficiency PSD powder diffractometer PSI (Zurich)
P. Fischer et al.




An Inexpensive but Effective PSD

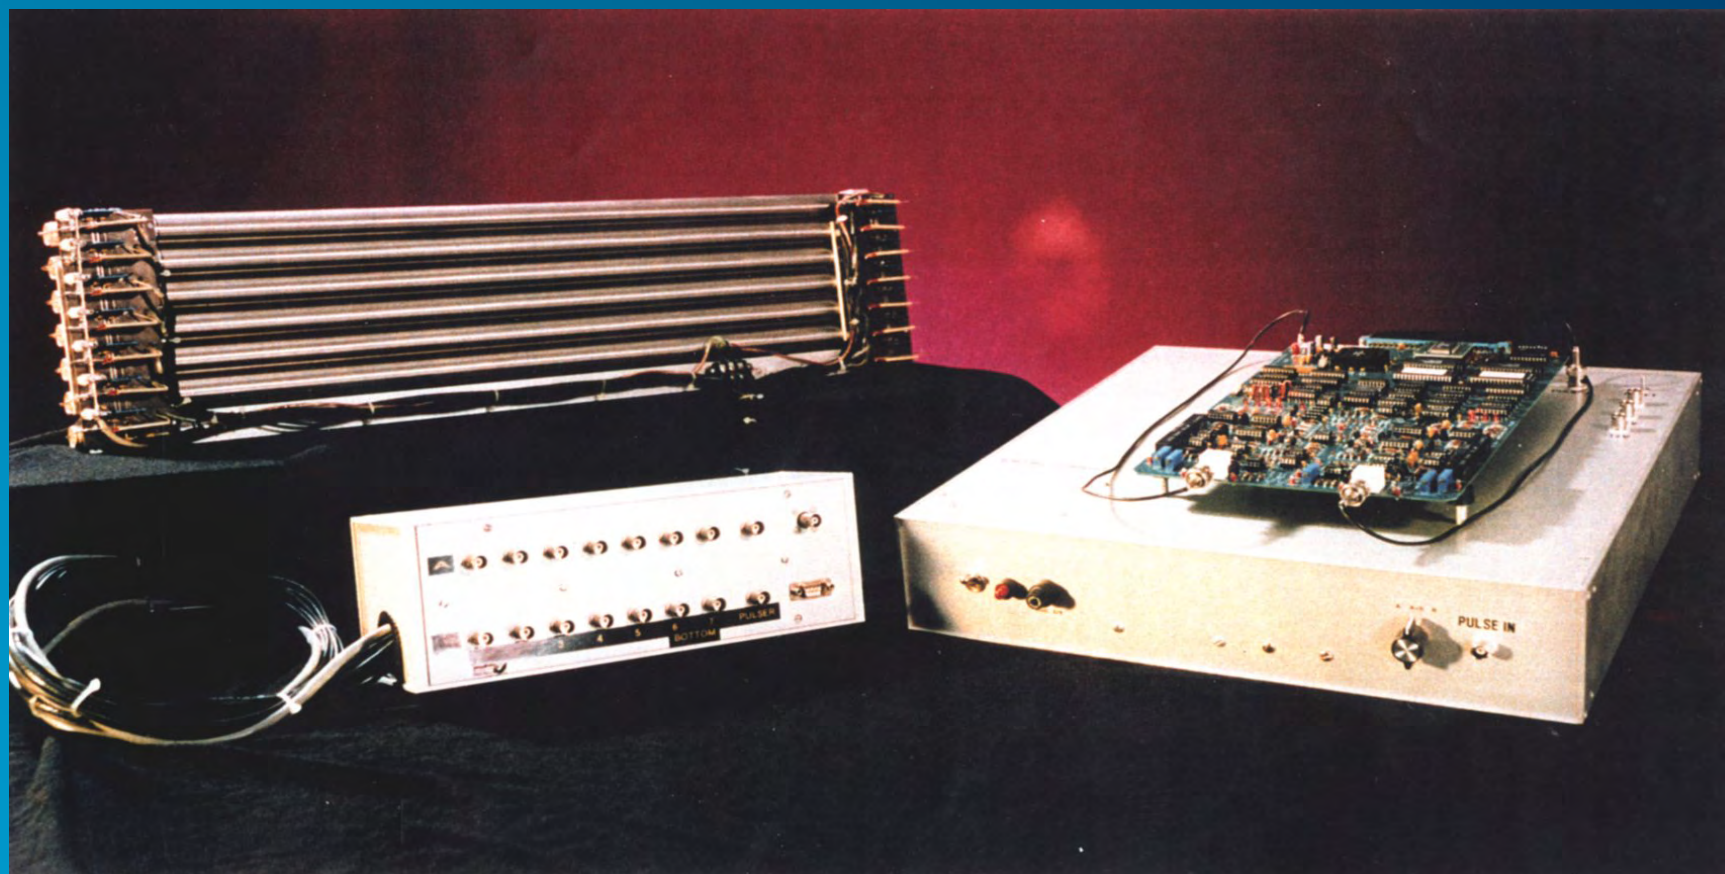

The liner wire PSD powder diffractometer at Kjeller, Norway.



State of the Art Powder Machines

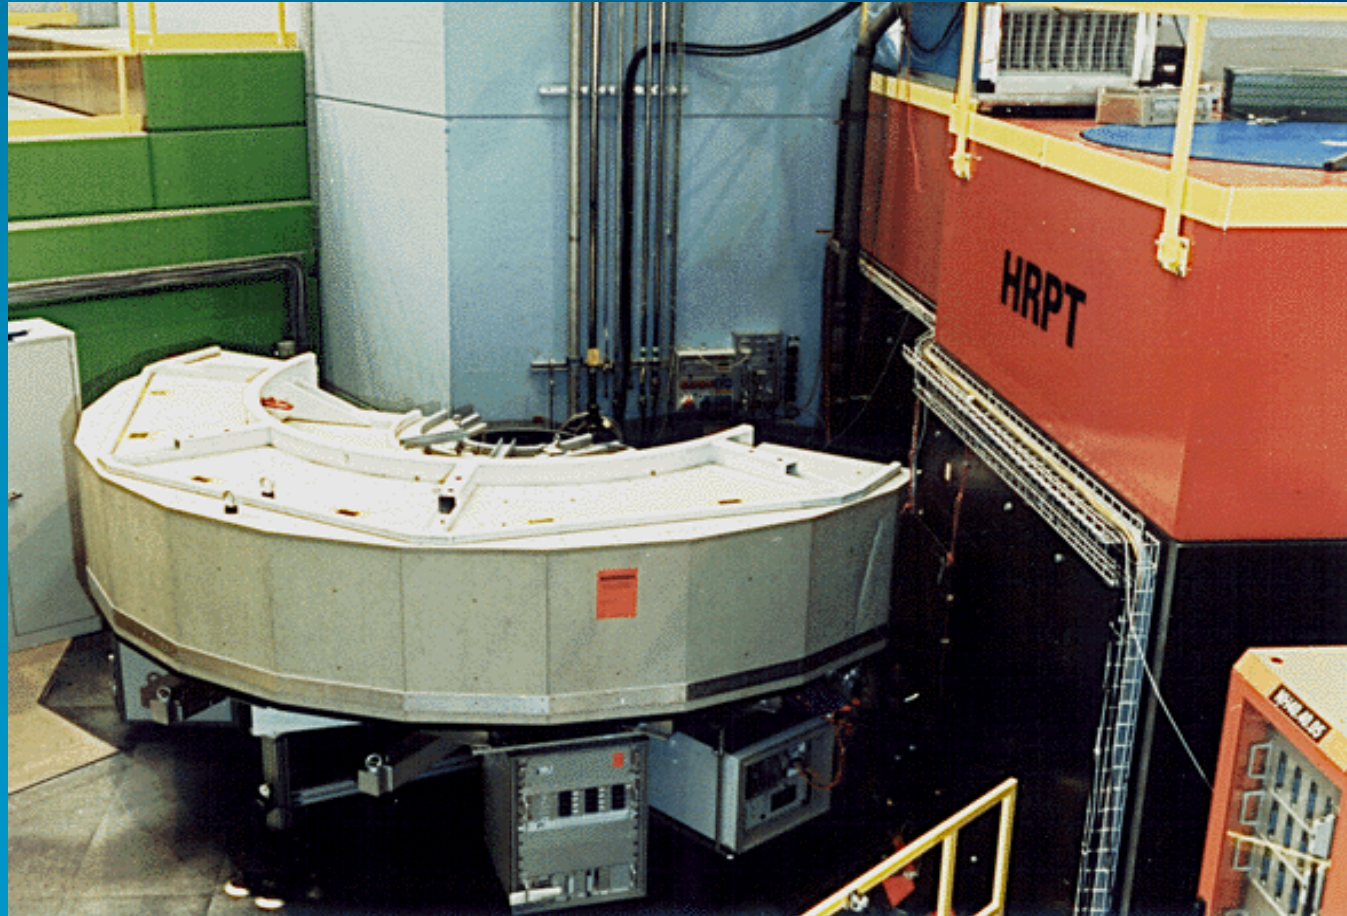


- HRPT 1600 cell PSD powder diffractometer at PSI (Zurich)
P. Fischer et al.



State of the Art Powder Machines


- HRPT 1600 cell PSD powder diffractometer at PSI (Zurich)
P. Fischer et al.

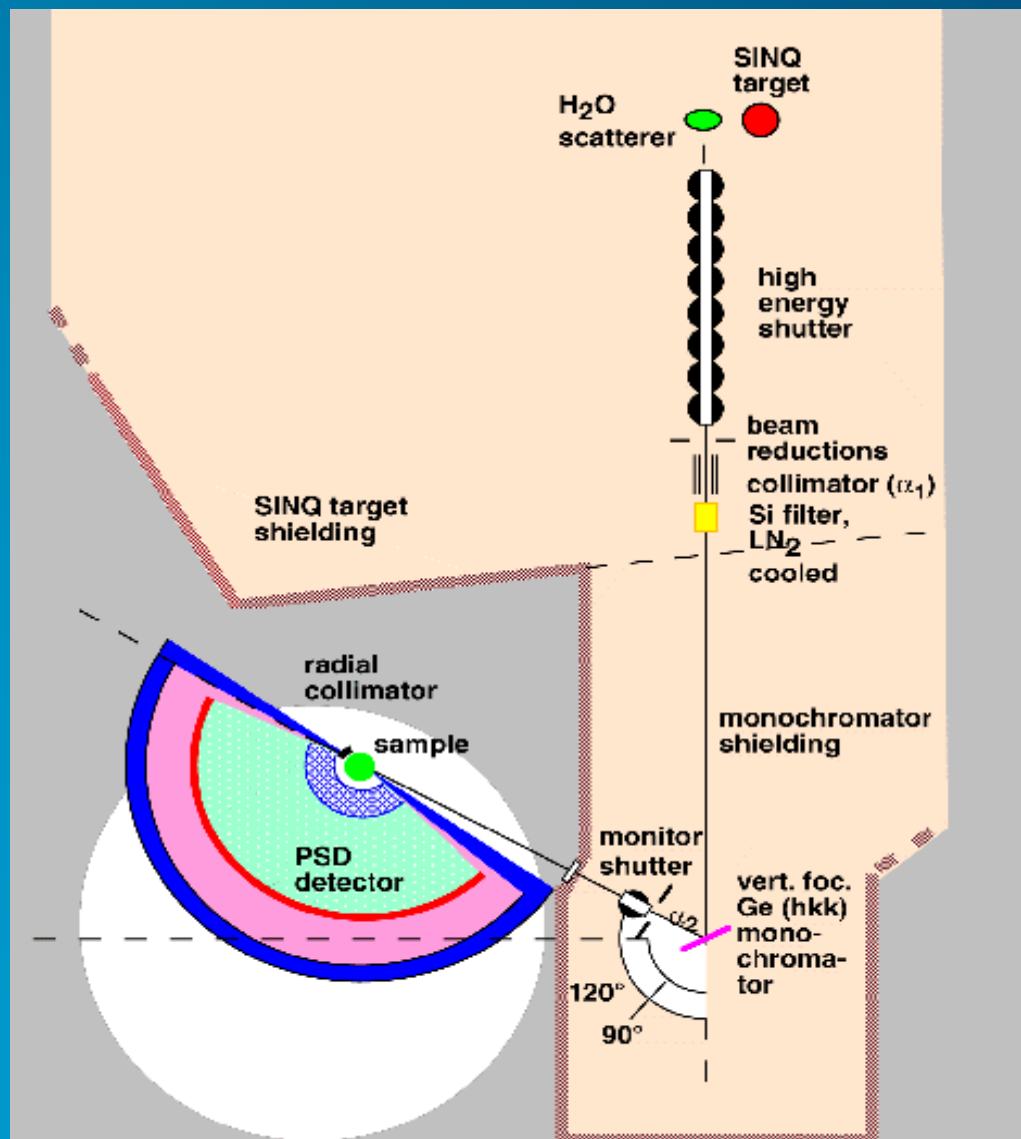



State of the Art Powder Machines


1600 wire PSD on a continuous spallation neutron source

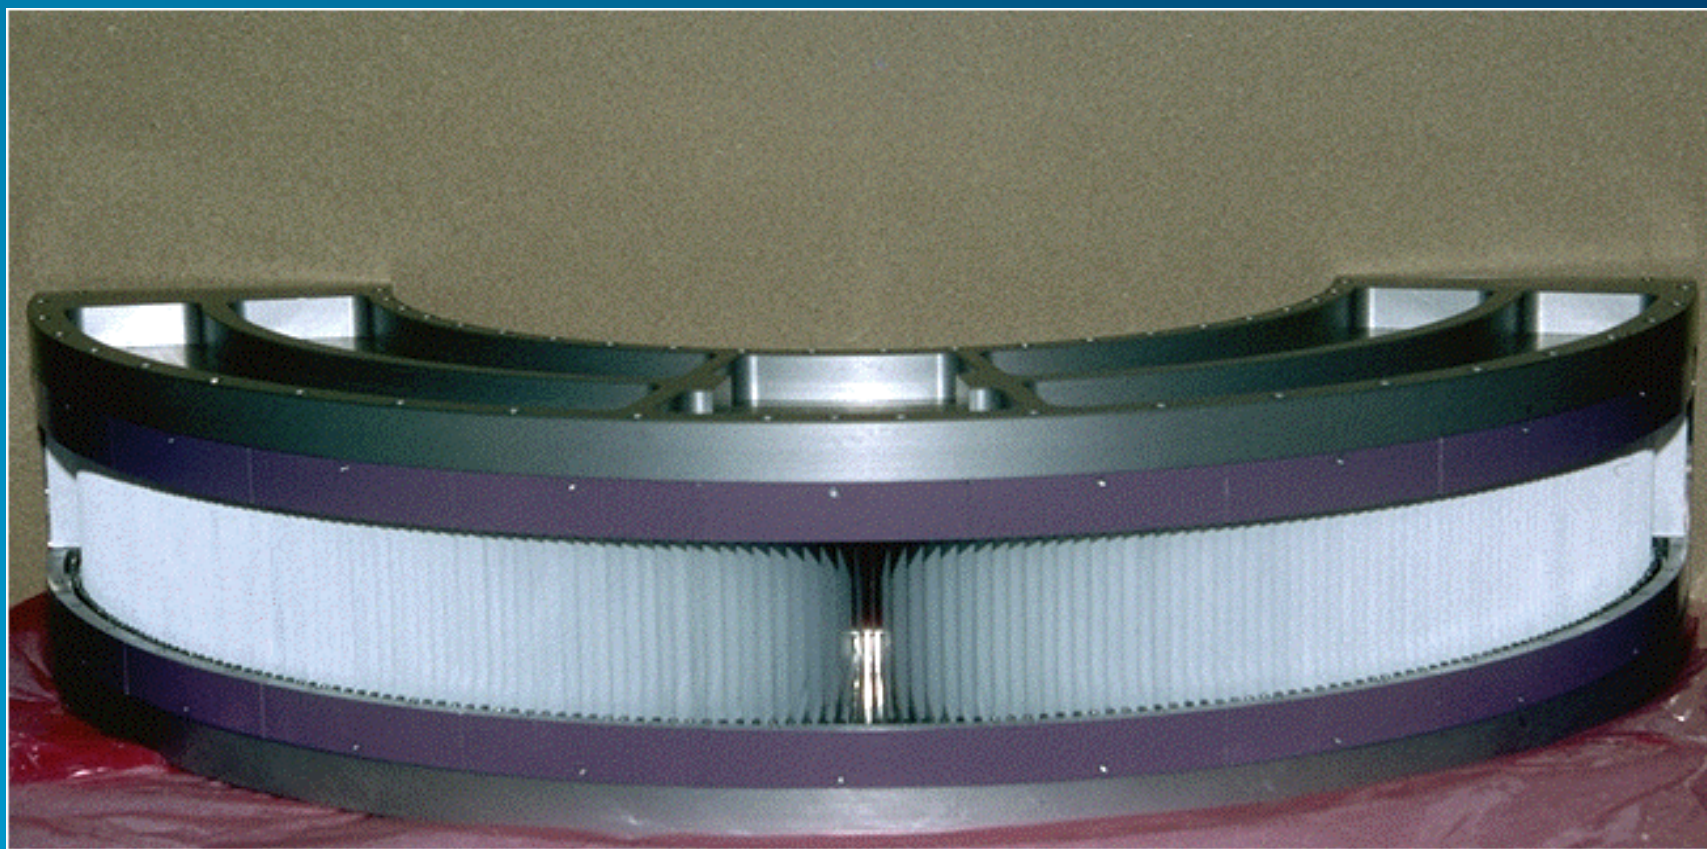

- Radial Collimator for new HRPT diffractometer at PSI Zurich (Fast, medium-high resolution machine) Peter Fischer et al.



Microstrip Detectors

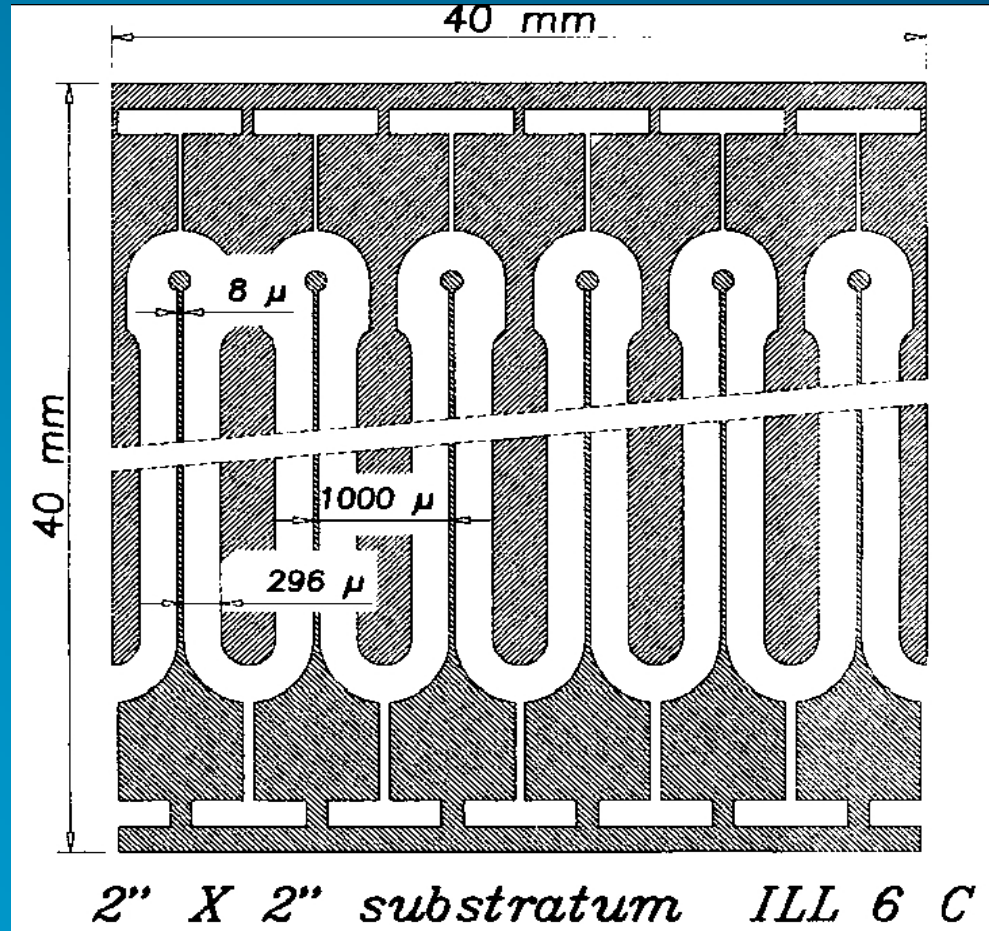


- The wires are replaced by a printed circuit on a glass substrate
- A high electric field is produced around the thin anodes.
- The glass substrate is electrically conducting to remove charge build-up

- PSD for 1600 element microstrip detector D20 at ILL Grenoble (Fast medium-high resolution machine) Pierre Convert et al.



What is a Microstrip Detector ?

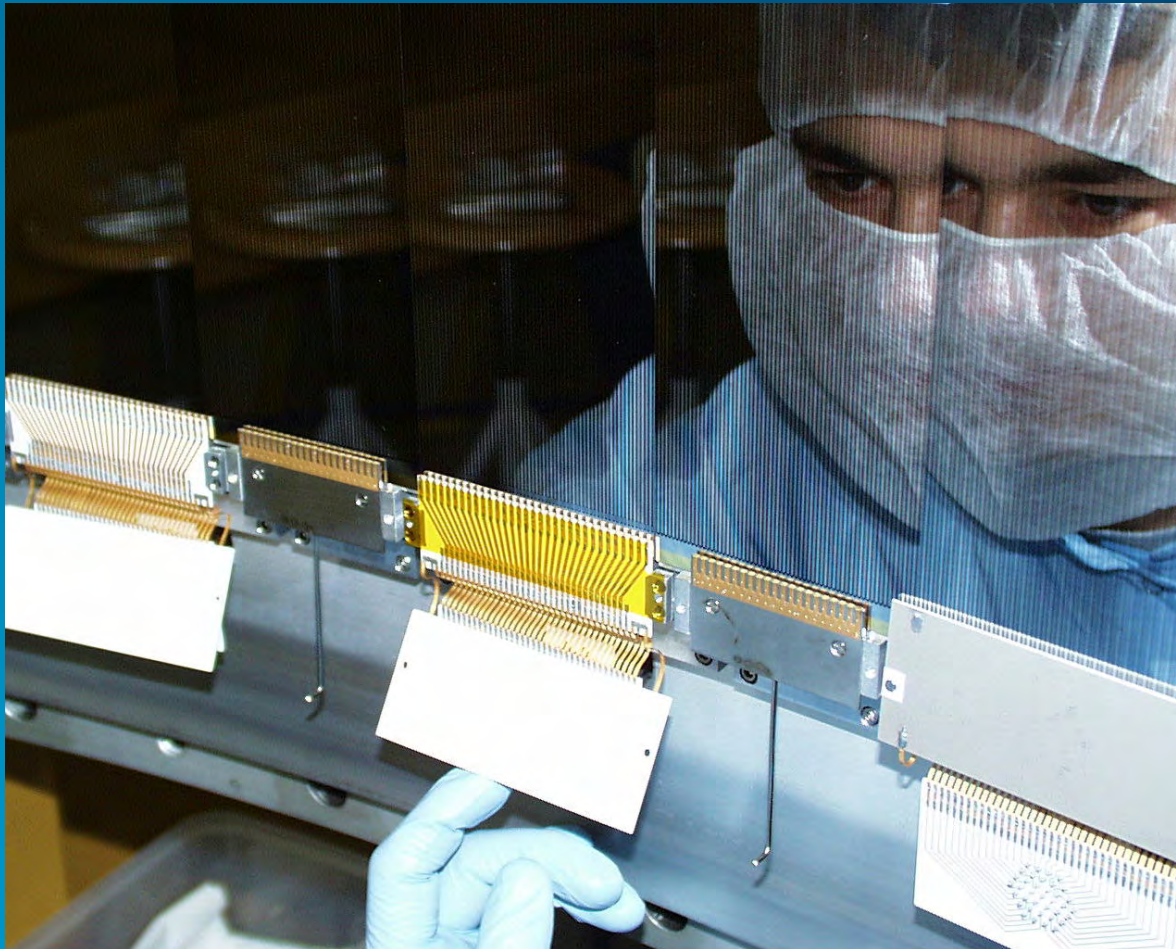


The printed circuit allows high resolution, mechanical stability...




ILL Grenoble

The Future - Big Detectors

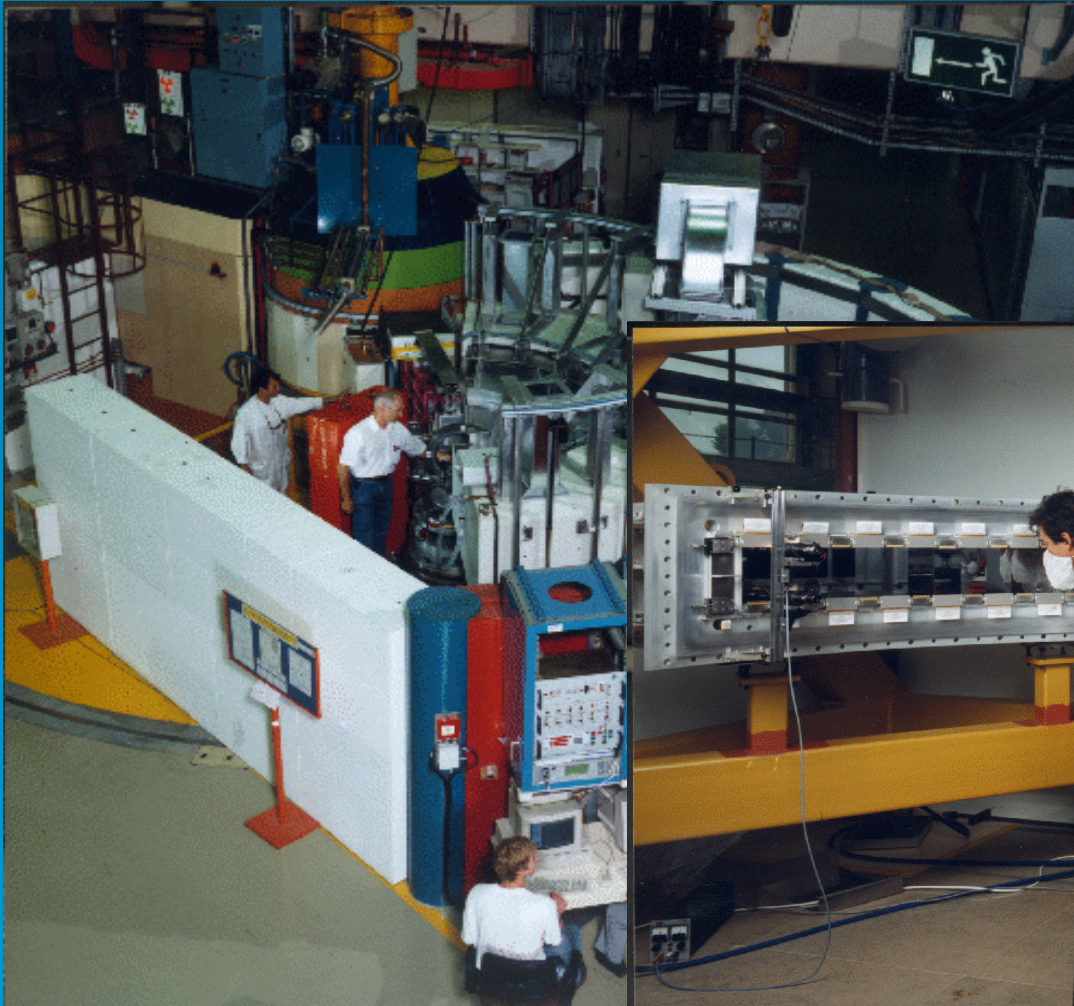


1600 element microstrip PSD on a continuous neutron source

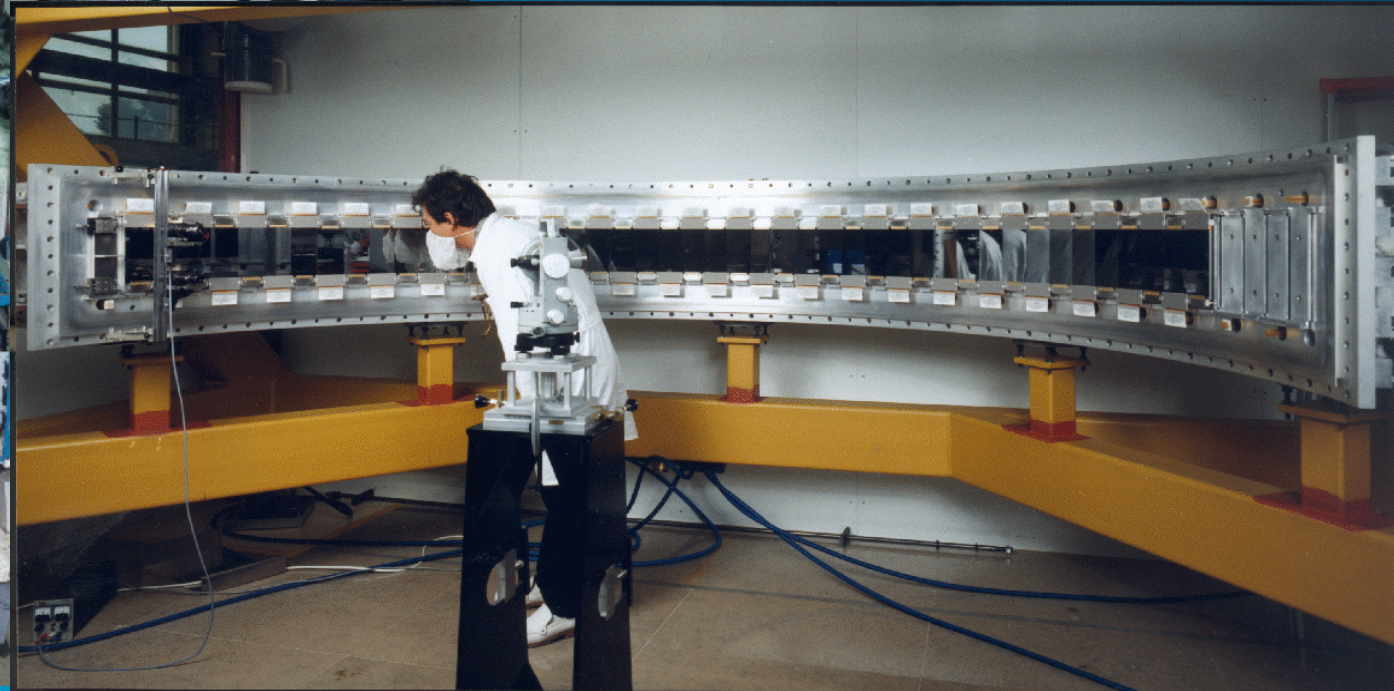

- Large 1600 element microstrip detector, D20 at ILL Grenoble (Fast medium-high resolution machine) Pierre Convert et al.



The Future - Big Detectors

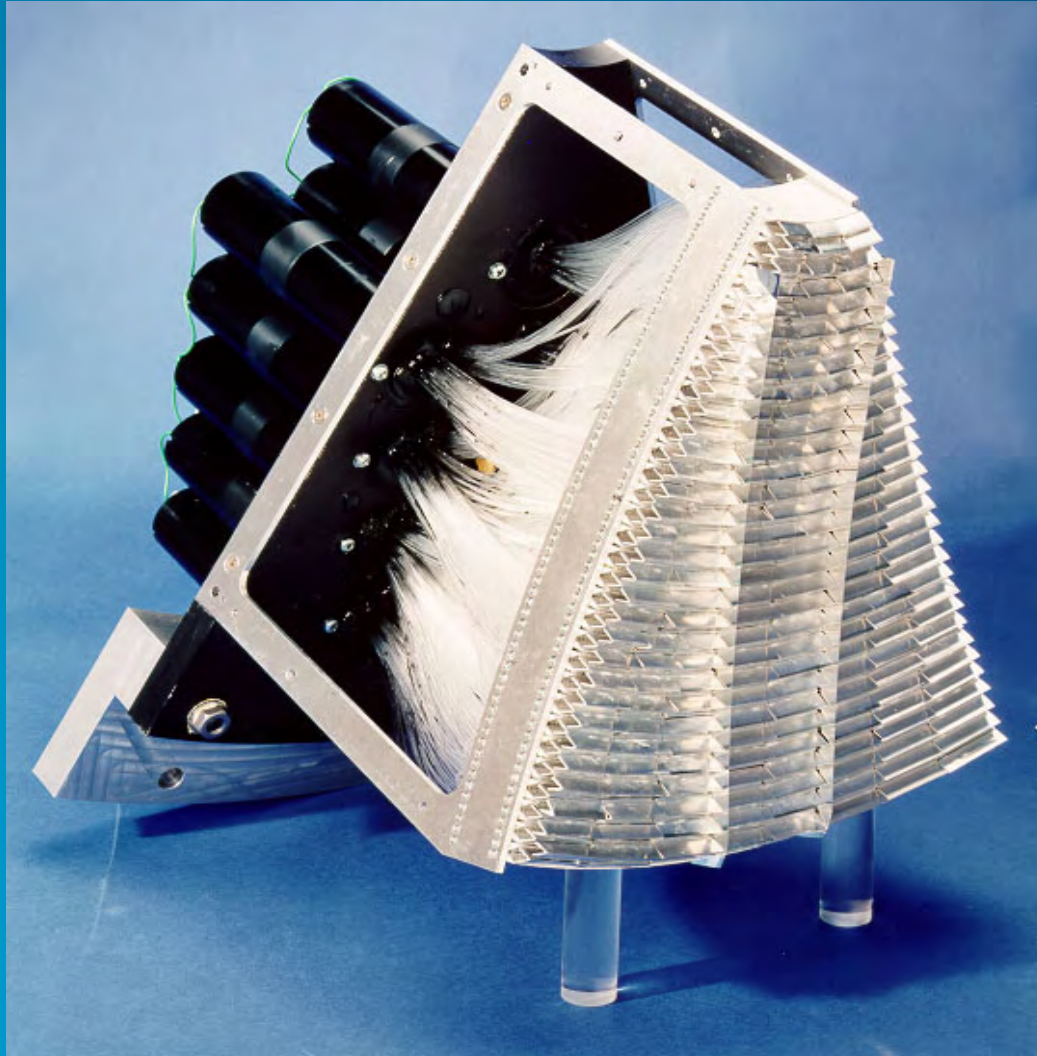


- HRPD & GEM, ISIS

- New scintillator detector element.
- Project for new 90° (medium resolution) detector bank



The Future - Big Detectors

Large detector array on a continuous neutron source

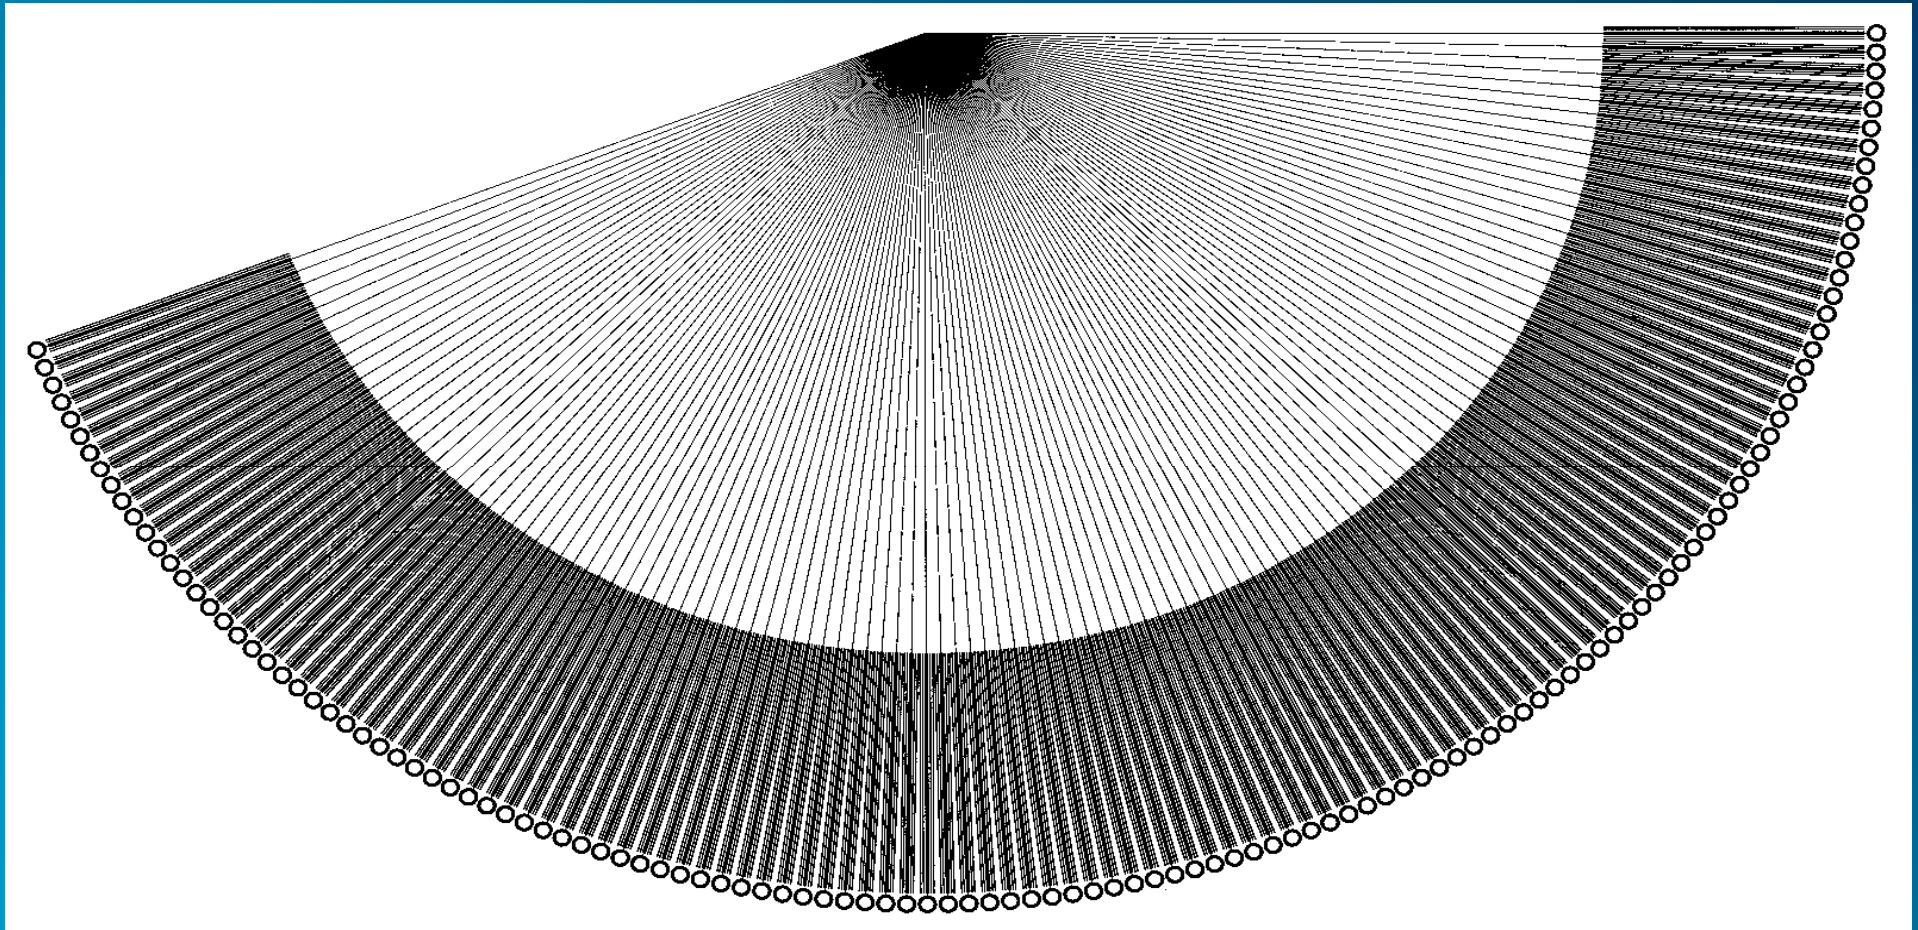


- Super-D2B at ILL Grenoble, very large high resolution detector



ILL Grenoble

New Munich Reactor FRM-II

SPODI Structure Powder Diffractometer cf super-D2B

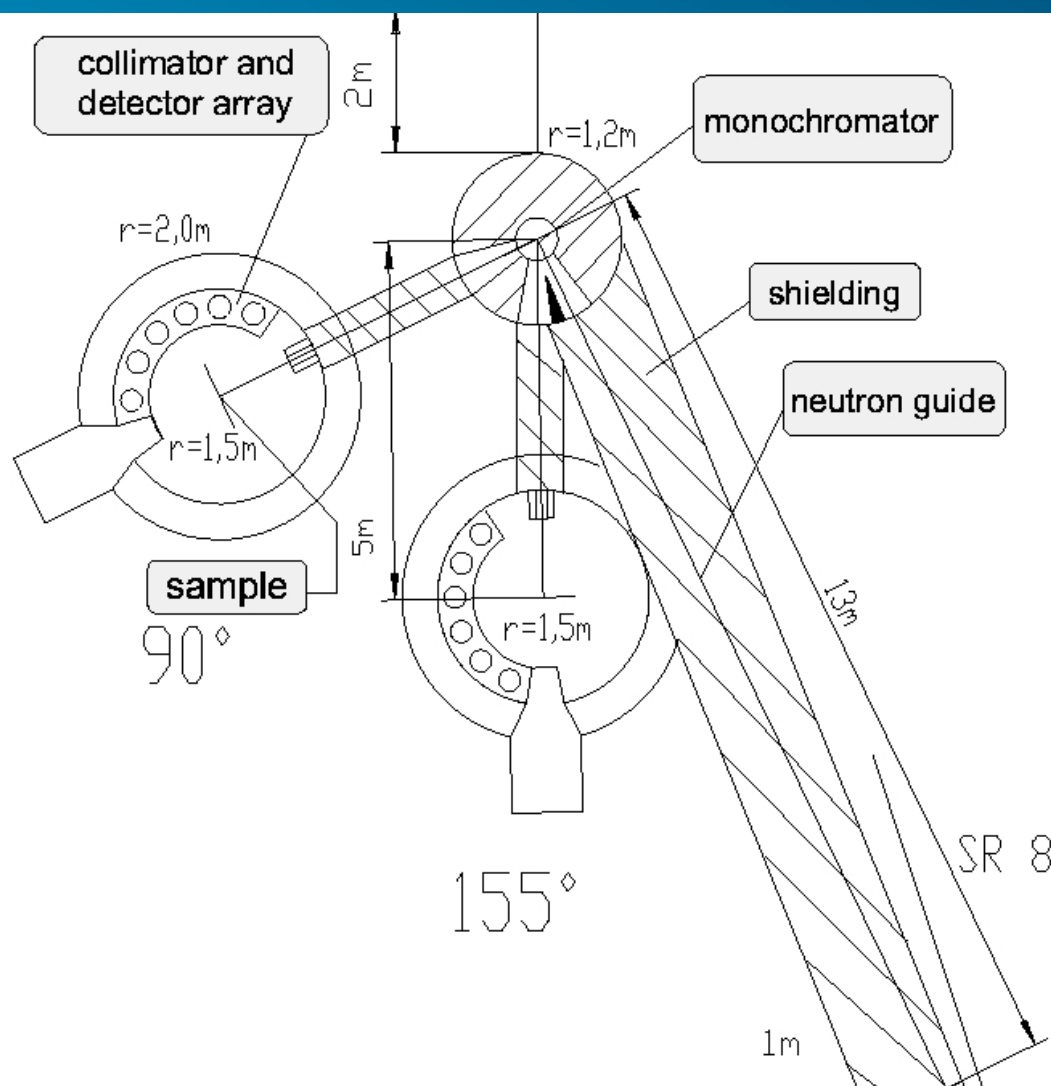


- Source distance 14.5m
 - Neutron supermirror guide
- Monochromator
 - Ge [551] vertical focus
 - Angle 90°, 135°, 155°
 - Mosaic 20'
- 80 Mylar 10' collimators
- 80 He3 detectors
 - 300 cm high
 - Linear wire PSD
- cf ILL super-D2B project.



Neutron Powder Diffraction

Real Materials, not crystals - Hydrogen in Metals

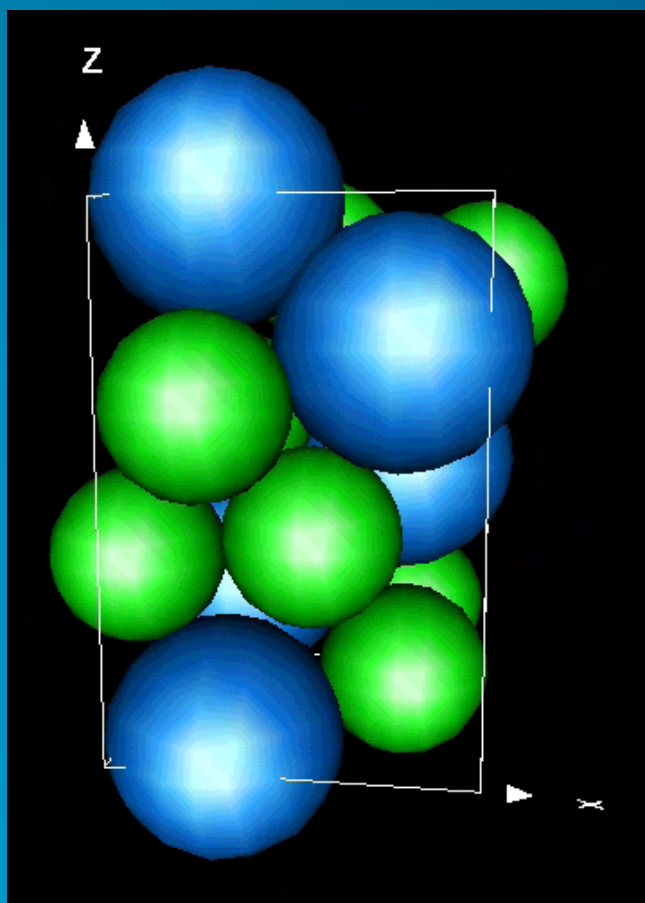

- Hydrogen storage in metals
 - Location of H among heavy atoms
 - No single crystals
- Laves phases eg LnMg_2H_7 (La, Ce)
 - Binary alloys with large/small atoms
 - Various stackings of tetrahedral sites -can be occupied by H-atoms
 - Up to 7 Hydrogens per unit
- Can even find H in Eu on D₂O !


Gingl, Yvon et al. (1997) J. Alloys Compounds **253**, 313.

Kohlmann, Gingl, Hansen, Yvon (1999) [Angew. Chemie](#) **38**, 2029. etc..



Neutron Powder Diffraction

Real Materials, not crystals - Hydrogen in Metals

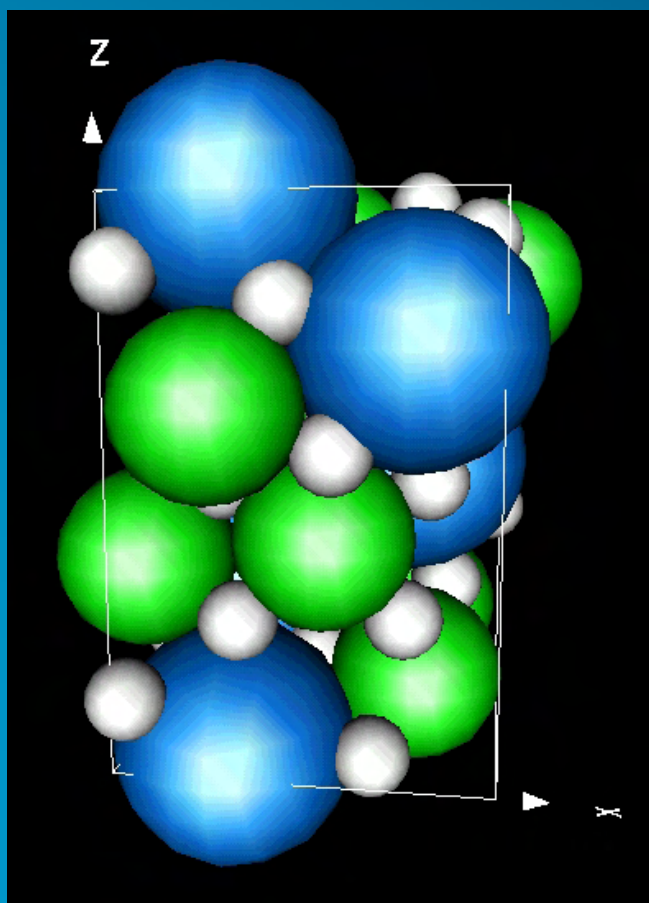

- Hydrogen storage in metals
 - Location of H among heavy atoms
 - No single crystals
- Laves phases eg LnMg_2H_7 (La, Ce)
 - Binary alloys with large/small atoms
 - Various stackings of tetrahedral sites -can be occupied by H-atoms
 - Up to 7 Hydrogens per unit
- Can even find H in Eu on D2O !


Gingl, Yvon et al. (1997) J. Alloys Compounds **253**, 313.

Kohlmann, Gingl, Hansen, Yvon (1999) [Angew. Chemie](#) **38**, 2029. etc..



High Pressure Powder Diffraction

New phases of Ice discovered by neutron diffraction

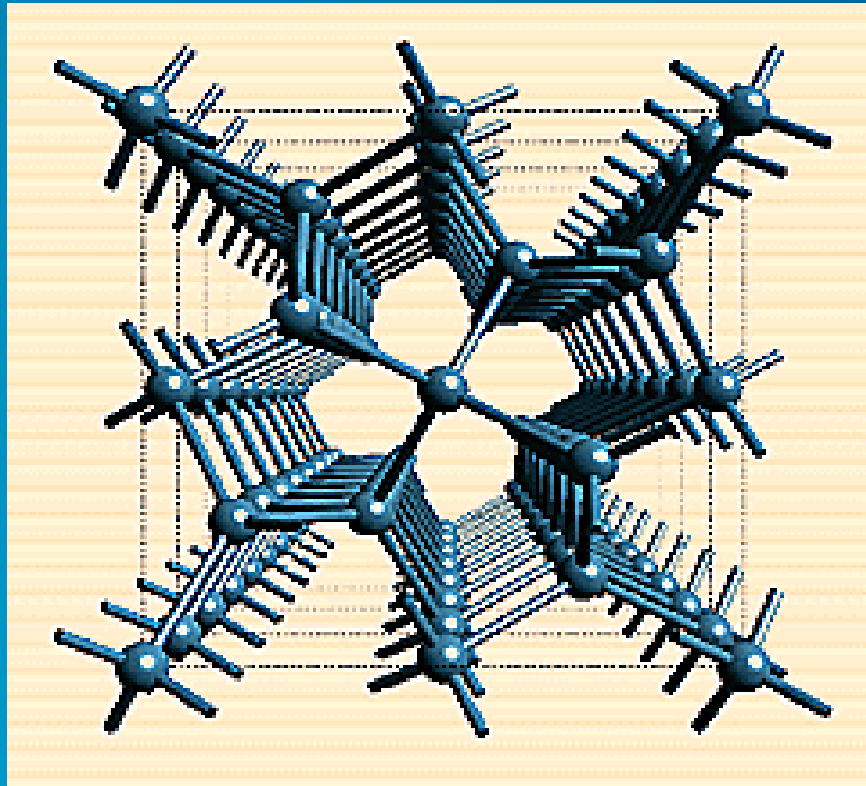

- Mixture of 5- and 7-membered rings of Ice XII.
- Delicate balance between competing ice phases - tests water potential functions in chemical & biological systems
- Model metastable structures


Lobban, Finney, Kuhs (1998) Nature 391, 268.

Kuhs, Lobban, Finney (1999) Rev.High Press.Sci.& Tech. 7.



High Pressure Powder Diffraction

New phases of Ice discovered by neutron diffraction

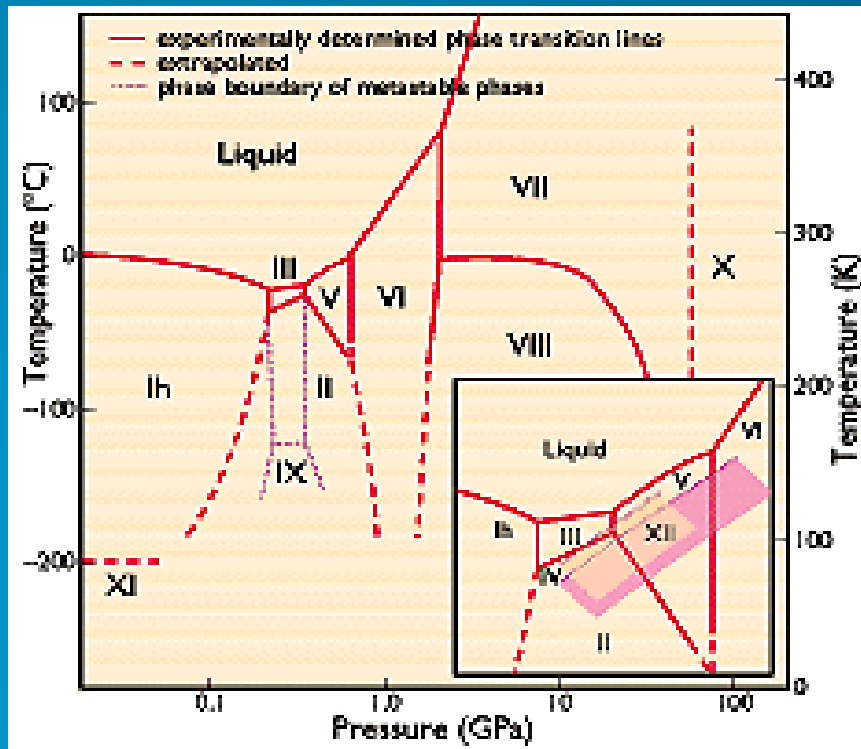

- Ice-XII - densest form of ice without interpenetration
- Ice-IV - auto-clathrate interpenetration of H-bonds for even higher density
- Ice-He clathrate like Ice-II

Lobban, Finney, Kuhs (1998) Nature 391, 268.

Kuhs, Lobban, Finney (1999) Rev.High Press.Sci.& Tech. 7.




Applications of large fast detectors

Real-time Phase Diagrams

Sue Kilcoyne, Bob Cywinski et al.

Crystallisation of amorphous alloys $\text{Y}_{67}\text{Fe}_{33}$ with increasing temperature

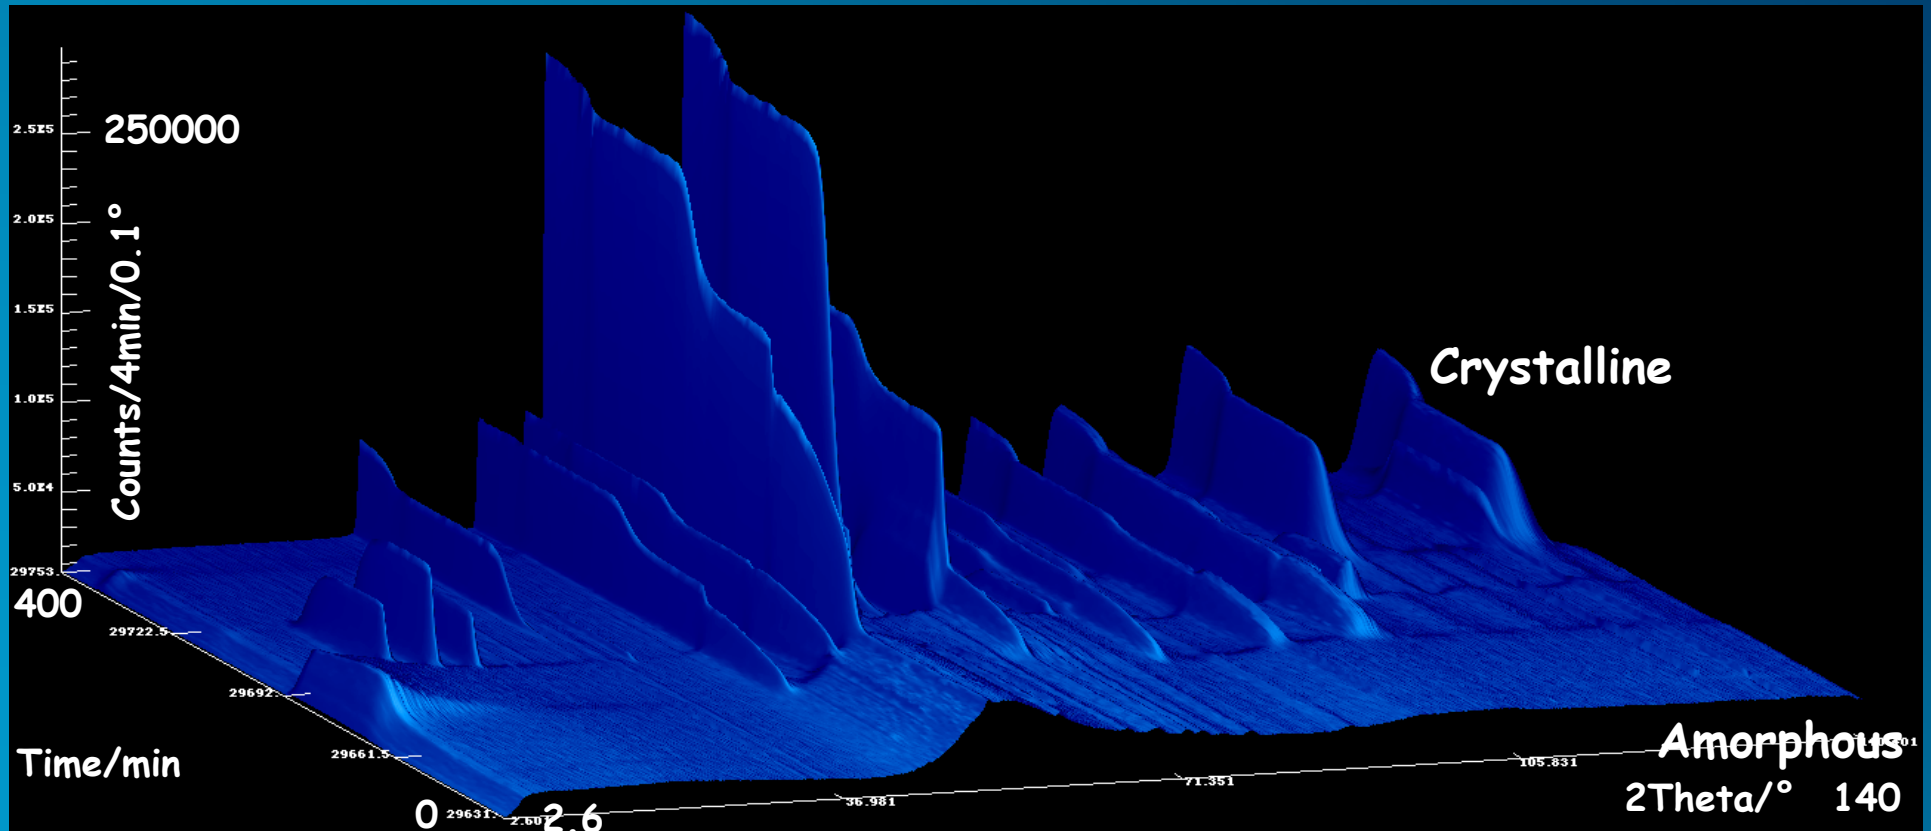

Complete diffraction pattern in minutes or seconds, scan through temperature






Applications of large fast detectors

Pseudo-binary RMn_2 compounds: $\text{Dy}_{1-x}\text{Y}_x\text{Mn}_2$

Clemens Ritter, R. Cywinski et al on D1B



ILL Grenoble

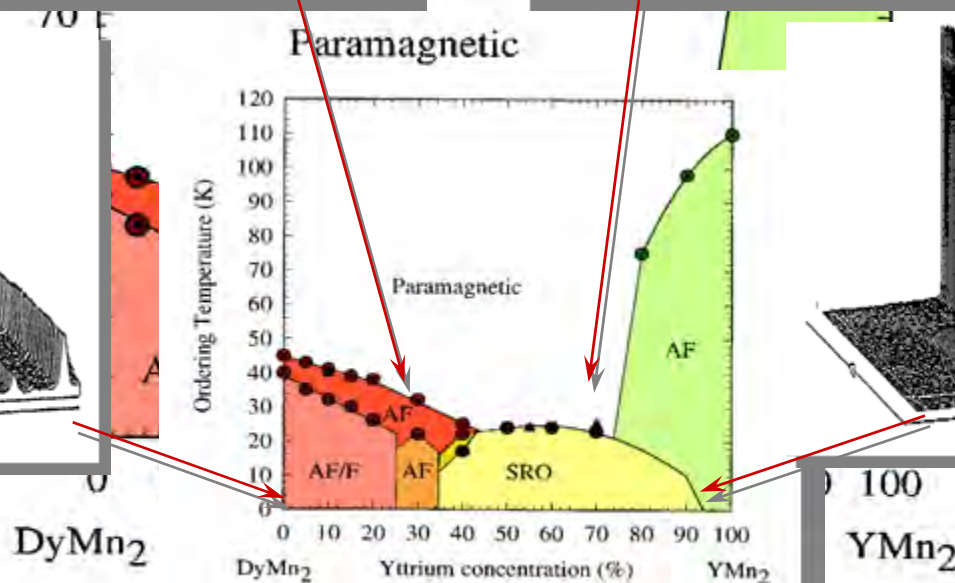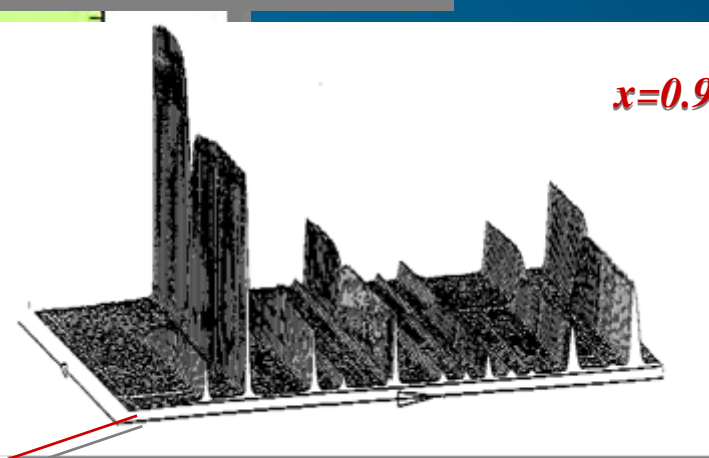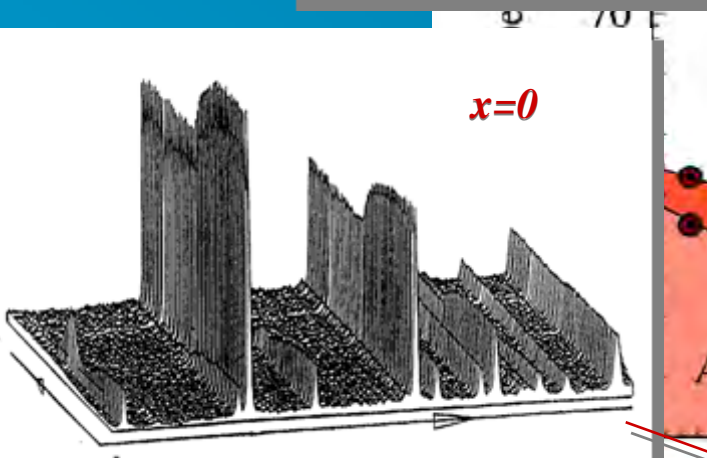
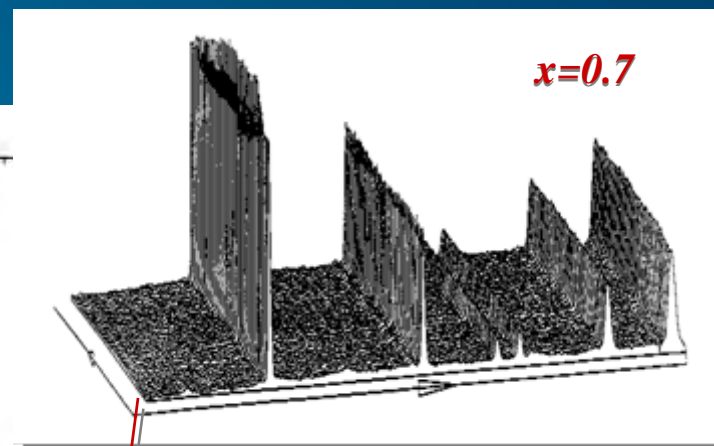
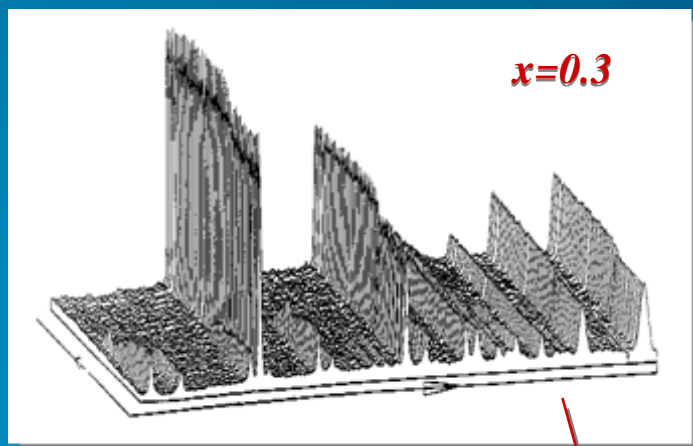




Applications of large fast detectors

Real-time electro-chemistry

- Latroche, Chabre et al.
In-situ Charging and discharging of metal hydride electrodes LaNi_5

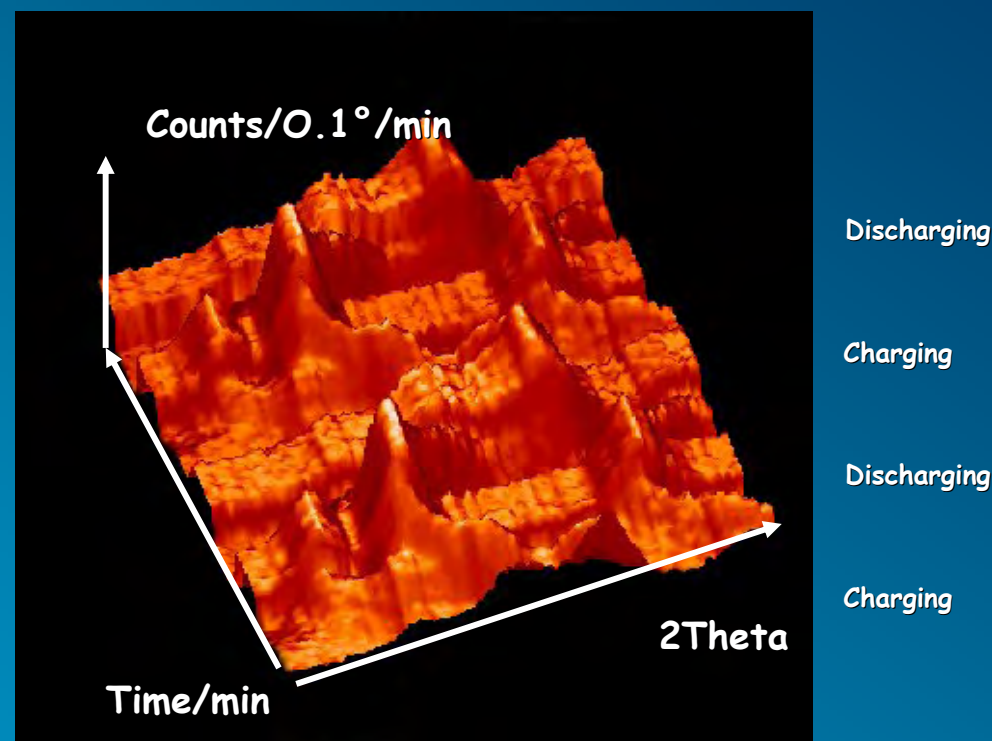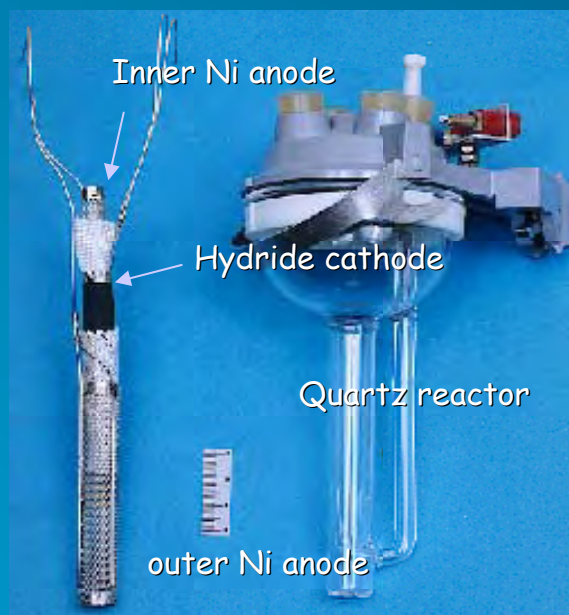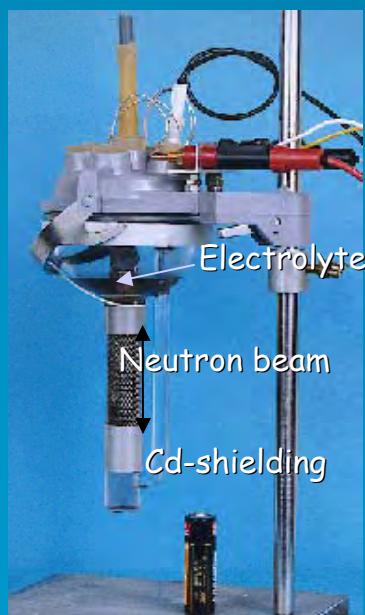


- Follow chemical changes with battery charge/discharge cycle



Valence Sum Calculations

What is the valence of Cu in Cu_4O_3 ?

O'Keeffe, M. Bovin, J. Am. Miner 63 180 (1978)


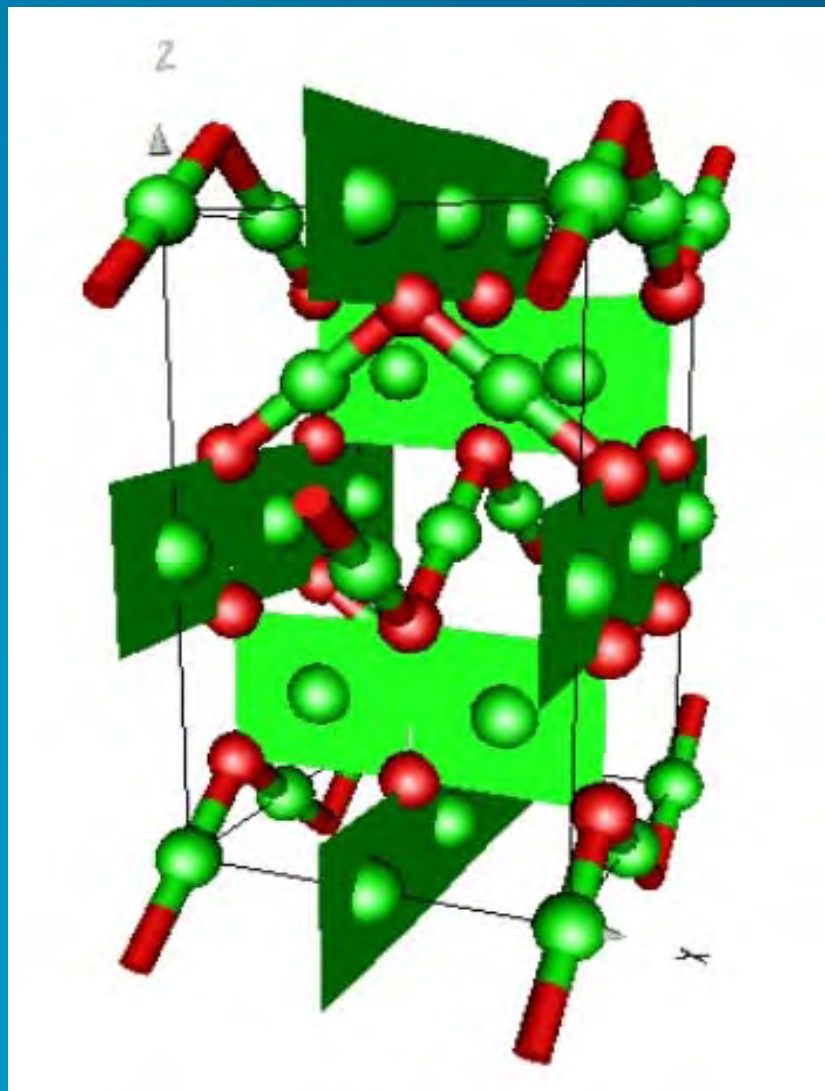


- Average Cu valence = $2 \times 3/4 = 1.5$
- 2 types of Cu
 - Cu^+ at (0,0,0) with 2 oxygens
 - Cu^{++} at (0,0,1/2) with 4 oxygens
- Valence Sum $V = \sum_i [\exp(\text{Ro} - \text{Ri}) / B]$
 - Ri = Cu-Oi bond lengths
 - $\text{Ro} = 1.610$ for Cu^+ to O^{2-}
 - $B = 0.370$
- Calculate Ri bond lengths & hence V



Electronic Order-Disorder

- Oxide superconductors, CMR, Vewey transition...
- Precise structural measurements vs temperature

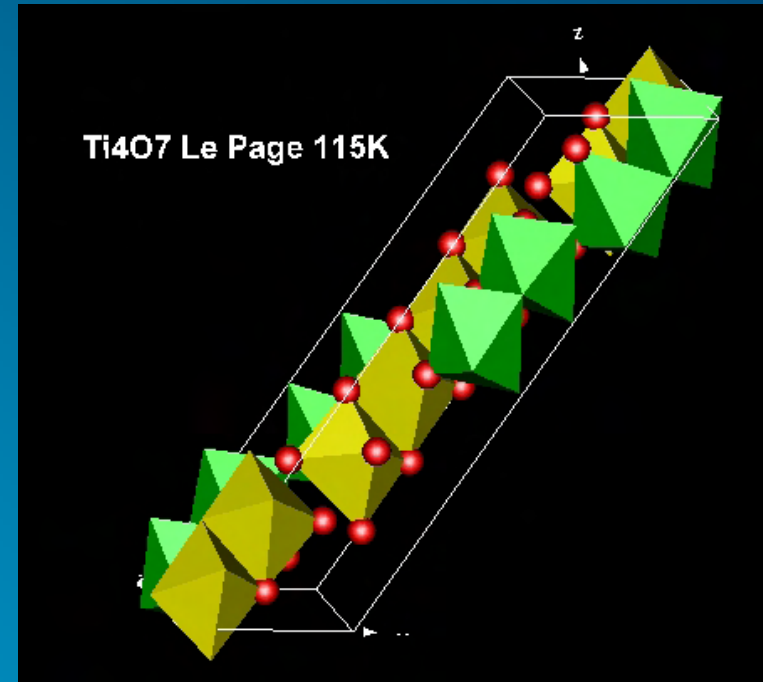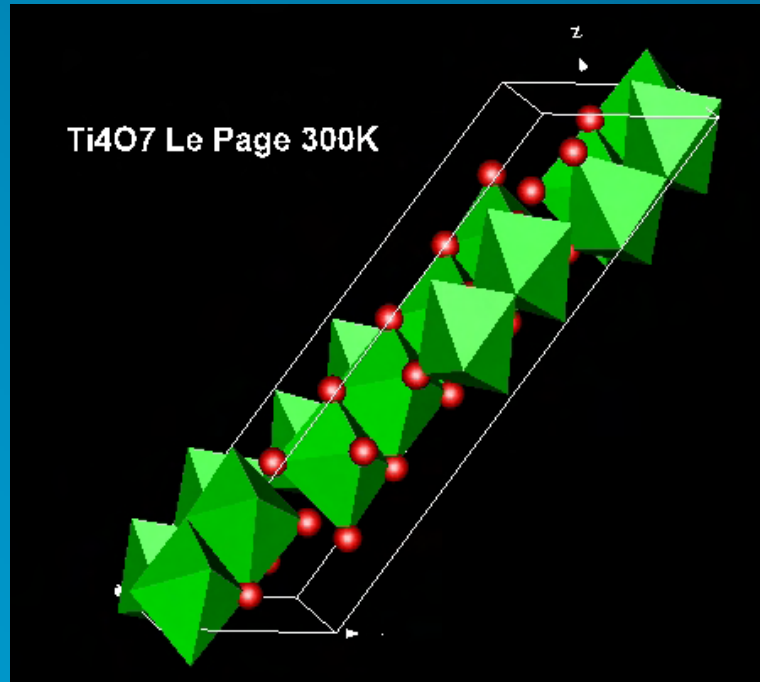

- Example: charge ordering in Ti₄O₇ (Le Page et al.

Neutron Powder Diffraction

Charge Transfer in YNiO_3

Marie-Theresa Fernandez-Diaz et al.


Alan Hewat




ILL Grenoble

Combined ESRF, D1B and D2B data - Alonso J.A. et al (1999) PRL 82, 3873

Metallic Ortho. $\text{YNiO}_3 \rightarrow$ Insulating Mono. YNiO_3 $T < 582\text{K}$ Ni valence $3-\delta$, $3+\delta$

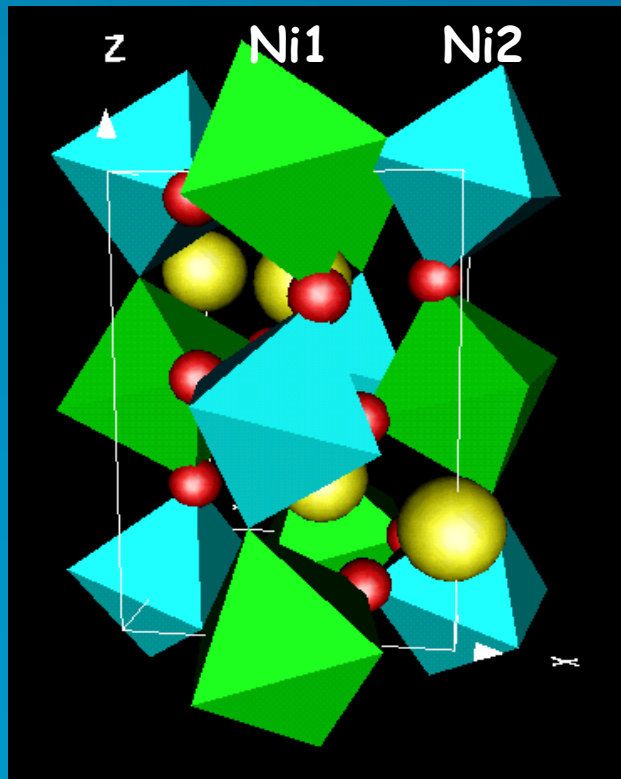

$$V(\text{Ni1}) = 2.62 \quad V(\text{Ni2}) = 3.17$$

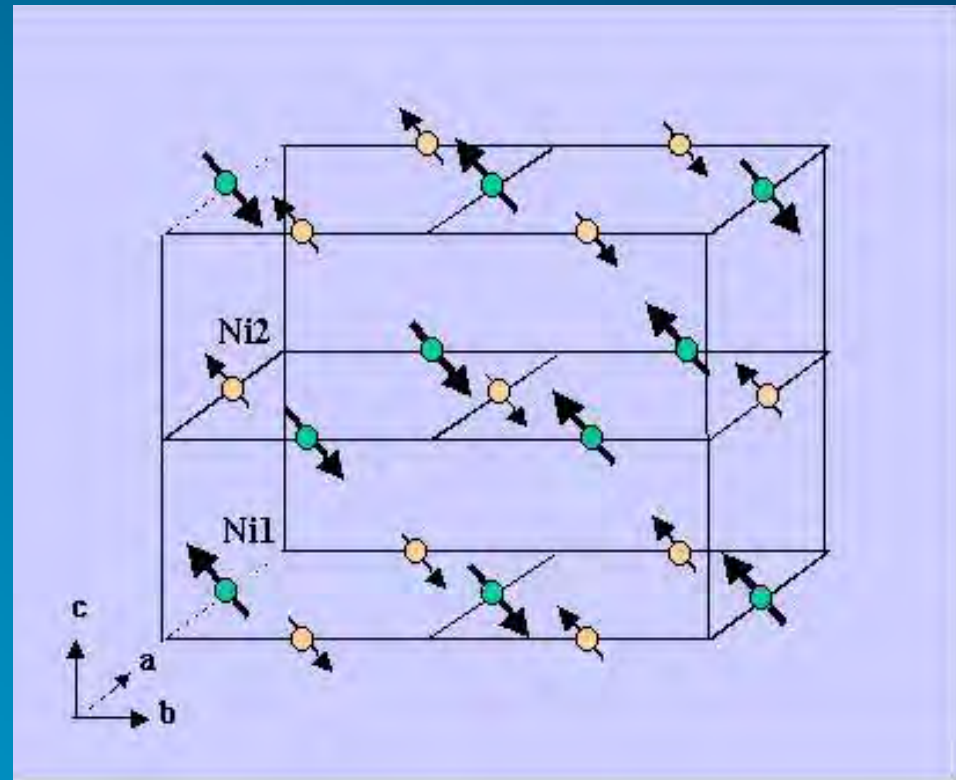


$$M(\text{Ni1}) = -1.4 \mu_B \quad M(\text{Ni2}) = 0.7 \mu_B$$

Neutron Powder Diffraction


Charge Transfer in YNiO_3

Marie-Theresa Fernandez-Diaz et al.

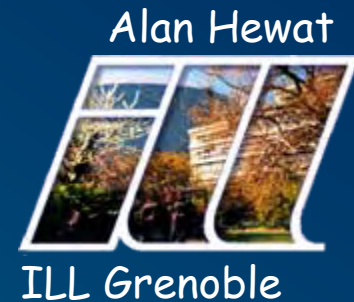

Combined ESRF, D1B and D2B data - Alonso J.A. et al (1999) PRL 82, 3873

Metallic Ortho. $\text{YNiO}_3 \rightarrow$ Insulating Mono. YNiO_3 $T < 582\text{K}$ Ni valence $3-\delta$, $3+\delta$

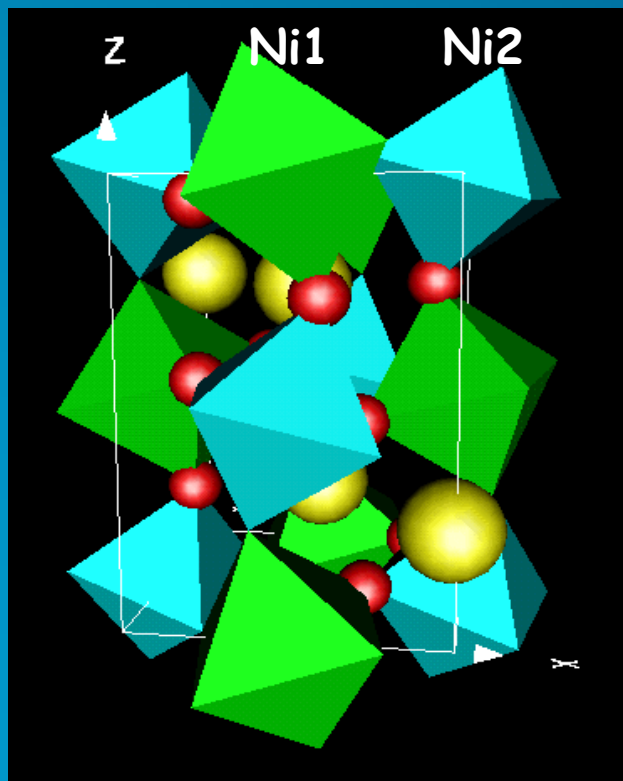


- Double evidence for charge transfer
 - Magnetic superstructure and different moments on Ni-sites
 - Different Ni-O distances around Ni1 and Ni2 sites mean 'charge transfer'
- Neutrons provide both. But need:
 - High resolution to resolve symmetry
 - High flux to see superstructure

$$V(\text{Ni1}) = 2.62 \quad V(\text{Ni2}) = 3.17$$



Giant Magneto-Resistive Ceramics

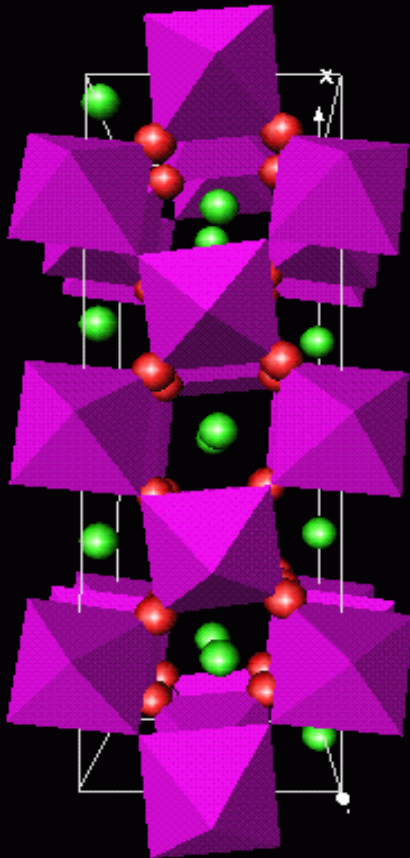


- Very large changes in electrical resistivity with temperature
- cf oxide superconductors
- mixed valence charge-ordering $\text{Mn}^{3+}/\text{Mn}^{4+}$
- GMR effect near room temperature
- applications to magnetic storage of data (new high density IBM hard disks)



GMR Stripes and Charge Ordering

1D-ordering ? Dimensionality important for theory.

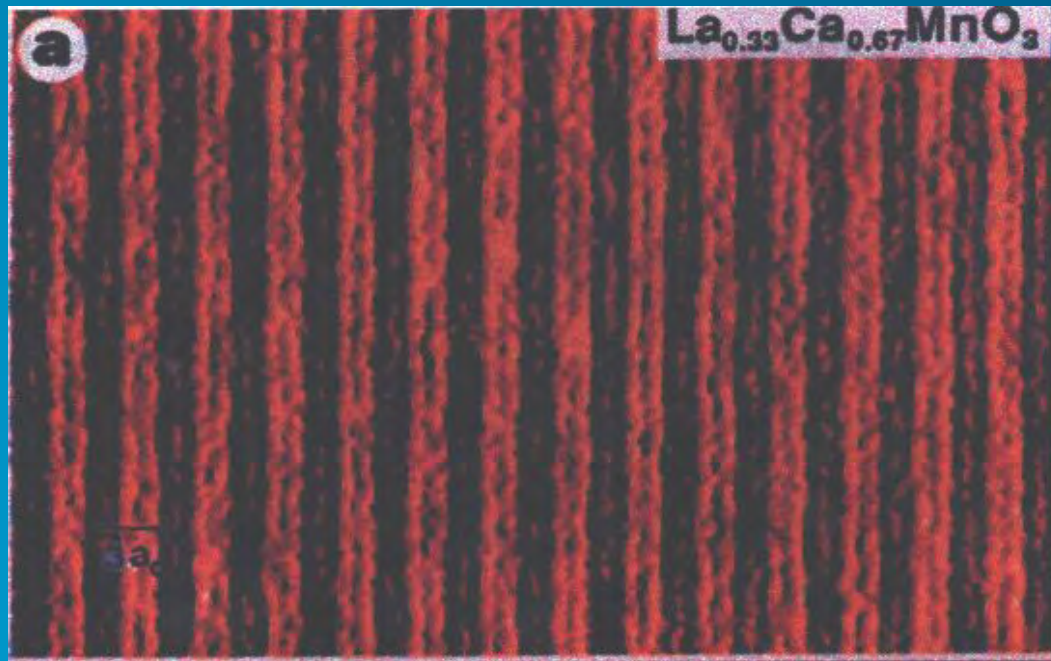


- Remarkable electron microscope images of 1D stripe pattern in GMR $\text{La}_{0.33}\text{Ca}_{0.67}\text{MnO}_3$
- Evidence also for 1D ordering in high- T_c superconductors (Cu^{3+} stripes, spin-ladders etc)

Mori et al. Nature (1998) 392,473
Other papers in Phys. Rev. Letters



GMR Stripes and Charge Ordering

1D-ordering ? Dimensionality important for theory.

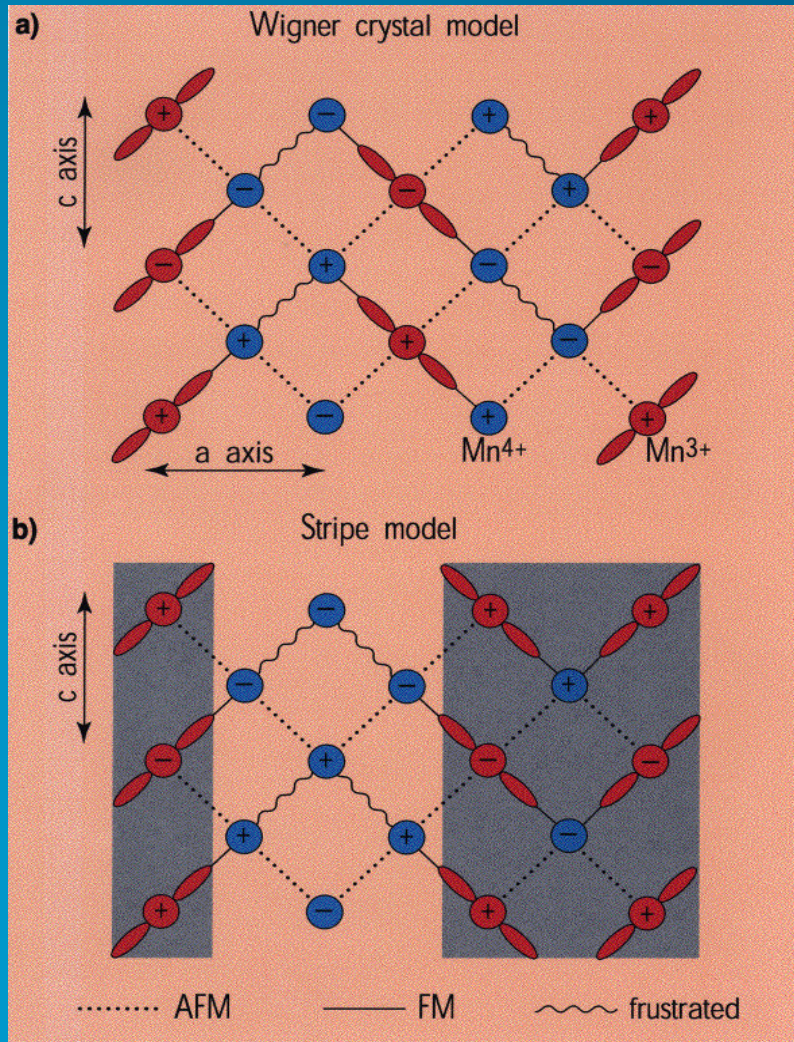


- Expect instead $\text{Mn}^{3+}/\text{Mn}^{4+}$ to be uniformly distributed (2D Wigner crystal model of Goodenough)
- The 1D-stripe model would have very important consequences for the theory of superconductors and GMR oxides



GMR Stripes and Charge Ordering

Neutron + Synchrotron Powder Diffraction

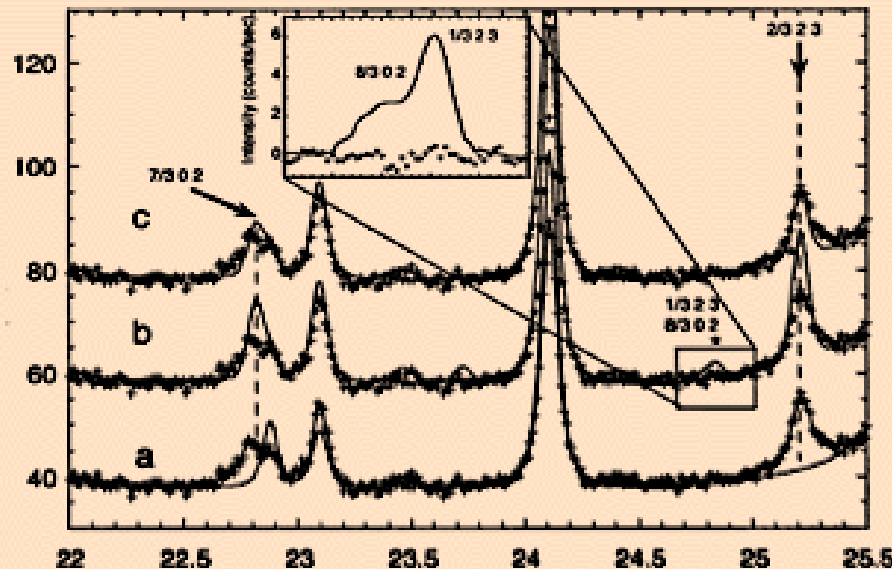

Radaelli et al. (1999) Phys. Rev B
X-ray work on X7A (BNL)
Neutron work on D2B (ILL)

- High resolution synchrotron powder data (Brookhaven) reveals true symmetry & ss
- High resolution neutron powder data (ILL Grenoble) allows refinement of real structure
 - a) Average Structure
 - b) Stripe Structure
 - c) Wigner Crystal Structure (best fit)
- The stripe structure is not supported



Neutron Powder Diffraction

- What has been achieved ? Exciting new science ?
 - High impact even outside the crystallographic community
 - Magnetism, Superconductors, Giant Magneto-Resistance
- Why Neutrons ? Why not X-rays ?
 - Neutrons+X-rays complementary
 - Solution of structures with X-rays
 - Refinement of important details with neutrons – valence sums
- Why Powders ? Why not crystals ?
 - Crystals should be used when available
 - Much new work started with powders – high T_c , GMR...